

Eliana Mitsue Takeshita

**AVALIAÇÃO DA AÇÃO DO
TRIMETAFOSFATO SOBRE O BIOFILME
DENTÁRIO, DESMINERALIZAÇÃO E
REMINERALIZAÇÃO DO ESMALTE:
ESTUDOS *IN VITRO* E *IN SITU*.**



Araçatuba – SP
2010

Eliana Mitsue Takeshita

**AVALIAÇÃO DA AÇÃO DO
TRIMETAFOSFATO SOBRE O BIOFILME
DENTÁRIO, DESMINERALIZAÇÃO E
REMINERALIZAÇÃO DO ESMALTE:
ESTUDOS *IN VITRO* E *IN SITU*.**

Tese apresentada à Faculdade de
Odontologia da Universidade Estadual
Paulista “Júlio de Mesquita Filho”, Campus
de Araçatuba, para obtenção de título de
Doutorado em Odontopediatria.

Orientador: Alberto Carlos Botazzo Delbem
Co-orientadora: Kikue Takebayashi Sasaki

ARAÇATUBA - SP

2010

Dados Curriculares

Eliana Mitsue Takeshita

Nascimento	28.12.1981 – Vitória – ES
Filiação	Milton Teiti Takeshita Cleusa Mitsuko Nonaka Takeshita
2000/2003	Curso de Graduação em Odontologia pela Universidade Estadual Paulista Julio de Mesquita Filho, Unesp – Campus Araçatuba.
2005/2006	Curso de Pós Graduação em Odontopediatria, nível de Mestrado, na Faculdade de Odontologia de Araçatuba – UNESP
2009	Estágio de Doutorado no Exterior no Academisch Centrum Tandheelkunde Amsterdam (ACTA)
2007/2010	Curso de Pós Graduação em Odontopediatria, nível de Doutorado, na Faculdade de Odontologia de Araçatuba – UNESP
Associações	CROSP - Conselho Regional de Odontologia de São Paulo SBPqO - Sociedade Brasileira de Pesquisa Odontológica

Dedicatória



À DEUS,

Presente em todos os momentos da minha vida, protegendo-me e guiando os meus passos em meu longo caminho rumo a grandes realizações. Devo a Ele todos os meus momentos de alegria e sucesso até aqui conquistado.

Muito Obrigada!

À MINHA “GRANDE FAMÍLIA”,

Por todos os conceitos divididos, ensinados e aprendidos. Pelo apoio e confiança em mim depositados em todos os momentos de minha vida. E que a distância fez provar a união que há entre nós.

AOS MEUS PAIS, MILTON E CLEUSA,

Confiança, determinação, dedicação, honestidade, cumplicidade, muita felicidade e amor. Simplesmente não há palavras que expressem meu amor por vocês.

AO MEU MARIDO FABIO,

Pela compreensão, amor, carinho e, mesmo longe, passou a segurança que precisava para terminar mais uma grande conquista. Amo muito você!

AOS MEUS IRMÃOS, WILTON E WILLIAM

Agradeço por serem meus queridos irmãos. E estarem sempre presentes em minha vida!

*“A única amizade que vale é aquela que nasce sem nenhum motivo”
Van Shendel*

AO MEU ORIENTADOR,

Prof. Dr. Alberto Carlos Botazzo Delbem, exemplo de docente e pesquisador. Pelo exemplo de ética, determinação, humildade e perseverança. Agradeço por todo o esforço que se dedicou a esse trabalho, e por ter me proporcionado esses anos de orientação. Aprendi muito estando ao seu lado.

Agradeço pela amizade, preocupação, compreensão e pelas grandes oportunidades a mim proporcionadas ao longo da nossa convivência.

Serei eternamente grata.

A PROF^a DR^a KIKUE TAKEBAYASHI SASSAKI,

Exemplo de dedicação, experiência, competência e ética. São inesquecíveis os momentos em que passamos juntos. Agradeço pela grande aprendizado e amizade de todos esses anos.

AO PROF BOB TEN CATE,

Toda a minha admiração. Agradeço por toda a sabedoria dividida no tempo em que pude aproveitar estando em seu grupo de pesquisa.

*“A primeira fase do saber, é amar os nossos professores”
Erasmus*

Agradecimentos Especiais



As alunas Luciene Pereira de Castro e Marcelle Danelon,

Pela ajuda na realização da fase laboratorial, e compreensão diante as exigências feitas por mim. E pela grande amizade.

Aos Voluntários dessa pesquisa,

Afonso Alexandre Correia, Aline Takamiya, Anderson, Douglas Roberto Monteiro, Lidiane Viana de Oliveira, Felipe Augusto da Silva Nishimoto, Fernanda Lourenção Brighenti, Ericlélia Crizóstomo Gomes Correia Coradini, Luciene Pereira de Castro, Marcelle Danelon, Paula do Prado Ribeiro.

“Para cada esforço disciplinado há múltiplas recompensas”
Jim Rohn

À Faculdade de Odontologia de Araçatuba, na pessoa dos professores Dr. Pedro Felício Estrada Bernabé, digníssimo Diretor e Dra. Ana Maria Pires Soubhia, digníssima Vice-Diretora, pela oportunidade de realizar toda minha carreira acadêmica, através do curso de graduação e pós-graduação.

Ao Curso de Pós-Graduação em Odontopediatria da Faculdade de Odontologia de Araçatuba – UNESP, na pessoa de seu coordenador Prof. Dr. Alberto Carlos Botazzo Delbem.

Aos docentes da Disciplina de Odontopediatria da Faculdade de Odontologia de Araçatuba, UNESP, Prof. Dr. Célio Percinoto, Prof. Dr. Robson Frederico Cunha, Profª Dra. Rosângela dos Santos Nery, Profª Dra. Sandra M. H. C. Ávila de Aguiar, exemplos de dedicação, pela agradável convivência e conhecimentos transmitidos.

A funcionária da Disciplina de Odontopediatria, Maria dos Santos Ferreira Fernandes, pelo grande esforço e dedicação ao Laboratório, agradeço o auxílio indispensável e pelos grandes momentos de descontração e carinho com todos os alunos.

Ao funcionário da Disciplina de Odontopediatria, Mario Luis da Silva, pelo auxílio e momentos de descontração.

À todos os colegas do curso de Pós-Graduação em Odontopediatria (Mestrado e Doutorado) da Faculdade de Odontologia de Araçatuba – UNESP, pela convivência carinhosa.

Aos amigos de turma de doutorado: Alessandra, Janaína, Max Douglas e Tais, pela convivência.

Aos amigos do Laboratório de pesquisa do Departamento de Odontopediatria pela convivência durante todo o doutorado: Adelisa, Amanda, Ana Paula, Ana Elisa, Ana Carolina (Tuca), Carla, Carol Lodi, Danielle, Eduardo, Emilene, Eliana Rodrigues, Fernanda, Gabriel, Jackeline, José Antonio, Isabele, Karina Mirela, Kélio, Lidiane, Lilian, Luciene, Marcelle, Marcelo, Michele, Cleide (Pity) e Rebeca.

Aos amigos do Laboratório de pesquisa da ACTA – Amsterdam: Alexa Laheij, Agnes de Fátima Faustino Pereira, Chi Pham, Derya Denis, Glauber Campos Vale, Mark Bujis, Michel, Rob Exterkate, Kiyoshi Tomiyama, Lei Cheng, Ricardo e Thiago Cruvinel Silva.

A Rob Exterkate por toda a compreensão e ajuda durante minha estada em Amsterdam. E por todos os ensinamentos na fase laboratorial dos trabalhos realizados no Laboratório de pesquisa da ACTA.

Aos amigos brasileiros de Amsterdam que tornou a distância do Brasil um pouco menor, Agnes, Ana Paula, Clarissa, Glauber e Thiago.

A Fernanda Lourenção Brighenti por ter me aconselhado nos momentos importantes durante a pós-graduação, e principalmente pela sua amizade.

A Eliana Rodrigues e Débora Barros Barbosa pela eterna amizade e confiança por todos esses anos.

A amiga Ana Carolina Soares Fraga Zaze, por participar de certa forma incentivando e dando apoio na realização desse trabalho, e por compartilhar na realização de outros trabalhos.

Ao aluno de iniciação científica José Antonio de Souza Santos, pelo auxílio para a realização de outros trabalhos.

Ao Departamento de Ciências Básicas, onde fui estagiária de iniciação científica durante a graduação.

Aos Demais professores e funcionários da Faculdade de Odontologia de Araçatuba – UNESP, em especial, Profª Dra Denise Pedrini, pelos ensinamentos transmitidos durante a graduação e pós-graduação.

Aos funcionários da Biblioteca da Faculdade de Odontologia de Araçatuba da UNESP, Ana Cláudia, Luzia, Ivone, Cláudio, Maria Cláudia, Izamar, Marina pela atenção e disponibilidade que nos recebem.

Aos funcionários da Seção de Pós-Graduação da Faculdade de Odontologia de Araçatuba-UNESP, em especial, Valéria e Diogo, pelo profissionalismo e atenção carinhosa dada a mim diante todas as dificuldades para a realização do Estágio PDEE.

Aos amigos que mesmo com a distância continuam sempre amigos: Aline, Bianca, Sayaka, Ioninha, Lívia, Solange, Marcelle, Fernando e Tatiana.

Ao Frigorífico Friboi, em especial, ao veterinário Henrique Borges, que permitiu a coleta dos dentes bovinos.

À Coordenadoria de Aperfeiçoamento de Pessoal de Nível Superior (CAPES), pela concessão de recursos que possibilitou a realização deste Curso de Doutorado e do Programa de Doutorado com Estágio no Exterior realizado em Amsterdam no Academisch Centrum Tandheelkunde Amsterdam – ACTA (PDEE, proc 463608-2).

À Fundação de Amparo a Pesquisa do Estado de São Paulo (FAPESP) pela Bolsa de Doutorado e auxílio concedido para a realização do trabalho. (procs. 07/03254-2, 07/03660-0)

À todos aqueles que, de certa forma, contribuíram para a elaboração e conclusão deste trabalho,

Minha gratidão eterna.....

SUCESSO

“Rir muito e com frequência; ganhar o respeito de pessoas inteligentes e o afeto das crianças; merecer a consideração de críticos honestos e suportar a traição de falsos amigos; apreciar a beleza, encontrar o melhor nos outros, deixar o mundo um pouco melhor, seja por uma saudável criança, um canteiro de jardim ou uma redimida condição social; saber que ao menos uma vida respirou mais fácil porque você viveu...

...Isso é ter tido sucesso”.

Ralph Waldo Emerson

Epígrafe



Resumo



Takeshita EM. Avaliação da ação do trimetafosfato sobre o biofilme dentário, desmineralização e remineralização do esmalte: estudos *in vitro* e *in situ* [tese]. Araçatuba: Universidade Estadual Paulista; 2010.

O uso de dentifrícios fluoretados por crianças menores de seis anos de idade é um fator de risco para a fluorose dentária. Uma maneira de diminuir a ingestão de fluoreto (F) seria reduzir a concentração desse íon; entretanto, é necessário manter a mesma efetividade de um dentifrício padrão (1100 µgF/g). Alguns estudos têm mostrado que dentifrícios suplementados com fosfato e cálcio são mais efetivos em prevenir a desmineralização e melhorar a remineralização. O objetivo do presente estudo foi avaliar o efeito do trimetafosfato de sódio (TMP) associado à baixa concentração de F sobre o biofilme, a desmineralização e remineralização do esmalte através de modelos de estudo *in vitro* e *in situ*. Para avaliação *in vitro* sobre des-remineralização do esmalte foi utilizado o modelo de ciclagem de pH. Blocos de esmalte (n=35) com lesão de cárie artificial foram submetidos a 15 dias de ciclagem de pH com 6 ciclos diários de 0,5 h em solução desmineralizadora e 2,5 h em solução remineralizadora. O tratamento foi realizado durante 5 min com soluções diluídas de 0, 500, 1500 ou 3000 µg F/g com ou sem a adição de 3% TMP. Após a ciclagem de pH os blocos de esmalte foram analisados através da microrradiografia (TMR) que mostrou a formação de lesão secundária nos grupos com baixa concentração de F. Essa lesão, entretanto, não foi observada nos grupos associados ao TMP. Para avaliação *in vitro* sobre o biofilme foi utilizado um novo modelo que possibilita a formação de biofilme de multi e simples espécies. Com essa finalidade foram testados diferentes substratos, vidro e esmalte de dente bovino e os tratamentos realizados com soluções de TMP associado ou não a antimicrobianos. Os resultados mostraram que em ambos os biofilmes de multi- e simples espécie, o TMP não altera a produção de ácido láctico nem a contagem de unidades formadoras de colônia. Para avaliação *in situ* sobre a des-remineralização do esmalte foram utilizados dois modelos de estudo. Para a avaliação sobre a desmineralização do esmalte *in situ*, 10 voluntários, utilizando dispositivo palatino com 4 blocos de esmalte bovinos selecionados através da dureza de superfície, foram submetidos a 4 fases experimentais de 14 dias cada. Os blocos de esmalte (n=160) foram alocados em 4 grupos de tratamento: placebo (controle negativo), dentifrício com 500 µg F/g,

dentifrício com 500 µg F/g e 1% TMP e um dentifrício com 1100 µg F/g (controle positivo). Durante o período experimental foram aplicados sobre os blocos: tratamento com dentifrício 2x/dia e uma solução de sacarose 20% 6x/dia. Após cada etapa, foi realizada a coleta do biofilme para análise da concentração de F, cálcio (Ca), fósforo (P) e polissacarídeos insolúveis extracelulares (EPS). Em cada bloco de esmalte, foram determinadas a alteração de dureza de superfície (%SH), perda integrada de dureza de subsuperfície (Δ KHN), e concentração de F, Ca e P. Os resultados mostraram que o dentifrício com F suplementado com 1% TMP apresentou a menor %SH ($p < 0,05$). Quanto à F e Ca no esmalte e biofilme não houve diferença entre dentifrício com 500 µg F/g e 1% TMP e controle positivo ($p > 0,05$), mas foram diferentes quando comparados ao dentifrício com 500 µg F/g e ao placebo ($p < 0,05$). Para avaliação sobre a remineralização do esmalte *in situ*, 11 voluntários, utilizando dispositivos palatinos com 4 blocos submetidos à lesão de cárie artificial, foram submetidos a 4 fases experimentais com duração de 3 dias cada. Os tratamentos foram realizados *in vivo* com os dentifrícios: placebo (controle negativo), 500 µg F/g, 500 µg F/g e 1% de TMP, e 1100 µg F/g (controle positivo); 3x ao dia por 1 minuto. Após cada período experimental, foi determinada a porcentagem de recuperação de dureza de superfície (%SH_R), Δ KHN e as concentrações de F, Ca e P no esmalte. Os resultados mostraram que os grupos controle positivo e 500 µg F/g 1% de TMP apresentaram similar %SH_R e Δ KHN ($p > 0,05$), porém diferentes dos grupos placebo e 500 µg F/g ($p < 0,05$). A concentração de F e P no esmalte foi semelhante nos grupos controle positivo e 500 µg F/g e 1% de TMP ($p < 0,05$). A concentração de Ca foi maior no grupo controle positivo ($p < 0,05$) seguido do grupo 500 µg F e 1% TMP. Com base nos resultados obtidos e considerando-se as limitações dos modelos utilizados, pode-se concluir que o TMP quando adicionado a um dentifrício de 500 µg F/g produz um efeito anticariogênico semelhante ao de um dentifrício de 1100 µg F/g, impede a formação da lesão secundária e que o TMP não apresenta atividade antimicrobiana.

Abstract



Takeshita EM. Evaluation of sodium trimetaphosphate (TMP) effect on biofilm and enamel de- and remineralization: *in vitro* and *in situ* study. [thesis]. Araçatuba: São Paulo State University; 2010.

The use of fluoridated dentifrices by children under 6 years old is a risk factor to dental fluorosis development. One way to reduce fluoride (F) ingestion would be the reduction of this ion concentration in dentifrices; however, it is necessary to maintain similar effectiveness to that of a standard dentifrice (1100 µgF/g). Some studies have demonstrated that dentifrices supplemented with phosphate and/or calcium are more effective in reduce the demineralization and increase the remineralization. The aim of this study was to evaluate the effect of TMP combined to low F concentration on enamel de- and remineralization and biofilm using *in vitro* and *in situ* models. To evaluate *in vitro* de- and remineralization, a pH cycling model was used. Bovine enamel specimens were submitted to 15 days of pH-cycling with a daily schedule of 6 cycles, each 0.5 h demineralization and 2.5 h remineralization. The treatment was performed for 5 min in aliquots of 30wt% dilutions of 0, 500, 1500 or 3000 µg F/g with or without the addition of 3% TMP. After the pH-cycling period the enamel specimens were analyzed by microradiography (TMR). The results showed that the TMR data showed that the formation of a second lesion in the low F groups. This phenomenon was not found in the TMP groups. To evaluate *in vitro* TMP effect on microcosm and single species biofilm, a new *in vitro* model was used. The experiments were carried out using different substratum, glass and enamel, and treatment was performed with antimicrobials with or without TMP. The results showed that in both microcosm and single species biofilm TMP did not alter lactic acid production and CFU counts. To evaluate *in situ* enamel de- and remineralization two different models were used. In the first model, 10 volunteers wearing acrylic palatal appliance containing four enamel bovine blocks selected through surface hardness, were submitted to 4 phases of 14 days each. The specimens (n=160) were allocated to four treatment groups: placebo, dentifrice with 500 µg F/g, dentifrice with 500 µg F/g TMP 1% and dentifrice with 1100 µg F/g. Dentifrices treatment was performed 2x/day, and 20% sucrose solution was applied 6x/day. After each experimental period, the biofilm was collected for F, calcium (Ca), phosphorus (P) and insoluble extracellular polysaccharides (EPS) analysis. In each enamel block, the percentage change of

surface hardness (%SH), integrated loss of subsurface area (Δ KHN), Ca, F and P content were determined. The results showed that the dentifrice with 500 F 1% TMP showed the lowest percentage change of surface hardness ($p < 0.05$). Regarding F and Ca in enamel and biofilm there were no differences between dentifrice with 500 TMP 1% and positive control ($p > 0.05$), but they were different when compared to dentifrice with 500F ($p < 0.05$). In the second model, eleven volunteers, wearing palatal appliance containing four bovine enamel blocks with artificial caries lesion, were subjected to 4 experimental phases during 3 days each. The treatment was carried out, *in vivo*, 3x/day during 1 min with dentifrices: placebo (negative control), 500F, 500F and TMP 1%, and 1100 μ gF/g (positive control). After each phase, the percentage of surface hardness recovery (%SH_R), Δ KHN, F, Ca and P content in enamel was determined. The results showed that the positive control and dentifrice with 500F and TMP 1% showed similar %SH_R and Δ KHN ($p > 0.05$), but they were different when compared to placebo and dentifrice with low-F ($p < 0.05$). Regarding F and P in enamel there were no differences between dentifrice with low-F and TMP 1% and positive control ($p > 0.05$). Ca content in enamel was higher in positive control ($p < 0.05$), followed by dentifrice 500F and TMP 1%. Based on this results and considering the limitations of the models used, we concluded that the addition of TMP to dentifrice with 500 μ g F/ g allowed similar anticariogenic effect to that of a standard dentifrice (1100 μ g F/g), and prevent the second lesion formation and TMP showed no antibacterial effect on microcosm and single species biofilm.

Listas



LISTA DE ABREVIATURAS

% =	Porcentagem
%SH =	Porcentagem de alteração dureza de superfície
%SH _R =	Porcentagem de recuperação de dureza de superfície
°C =	Graus Celsius
μ =	Micro
μg =	Micrograma
μg F/g =	Micrograma de fluoreto por grama
μg /mm ³ =	Micrograma por milímetro cúbico
μL/g =	Microlitro por grama
μm =	Micrômetro
ADA =	American Dental Association
Al ₂ O ₃ =	Óxido de alumínio
BHI =	Brain Heart Infusion
Ca =	Cálcio
CaF ₂ =	Fluoreto de cálcio
CaCl ₂	Cloreto de cálcio
CFU =	Unidades formadoras de colônia
CHX =	Clorexidina
CPC =	Cloreto de cetilpiridínio
CPW =	Cysteine peptone water
CO ₂ =	Dióxido de carbono
ΔKHN =	Perda integrada da dureza de subsuperfície
EPS	Polissacarídeos insolúveis extracelulares
F =	Fluoreto
FI =	Flúor iônico
FT =	Flúor total
g =	Aceleração da gravidade
h =	Hora
H ₂ =	Hidrogênio
HCl =	Ácido clorídrico
H ₂ O =	Água

IML =	Integrated Mineral Loss
KCl =	Cloreto de potássio
KH_2PO_4 =	Fosfato dihidrogenado de potássio
KHN =	Unidade de dureza Knoop
mL =	Mililitros
mL/mm^3 =	Mililitros por milímetro cúbico
mm =	Milímetros
mm^2 =	Milímetros quadrados
Mol/L =	Molaridade
n =	Número da amostra
N_2 =	Nitrogênio
NaCl =	Cloreto de sódio
NaF =	Fluoreto de Sódio
NaOH =	Hidróxido de Sódio
OH =	Hidroxila
P =	Fósforo
Pi =	Fosfato inorgânico
PBW =	Buffered peptone water
pH =	Potencial hidrogeniônico
pK =	Potencial de ionização
ppm =	Partes por milhão
s =	Segundos
SD =	Standard deviation
SH =	Dureza de superfície inicial
SH_1 =	Dureza de superfície pós-cárie
SH_2 =	Dureza de superfície final
TISAB =	Tampão de ajustador de força iônica total
TMP =	Trimetafosfato de Sódio
TMR =	Microrradiografia transversal
TSA =	Tryptic (Trypticase) Soy Agar
W =	Watts

LISTA DE FIGURAS

FIGURAS CAPÍTULO 1

- Figure 1 - Average mineral content profiles (vol% mineral versus depth) recorded from microradiographs taken from specimens of lower (Panel A) and higher fluoride groups (Panel B), both with and without. 46

FIGURAS CAPÍTULO 2

- Figure 1 - Lactic acid data (A) and Colony Forming Unit (CFU counts) (B) from experiment 1. 57

FIGURAS CAPÍTULO 3

- Figure 1 - **A** Enamel blocks selection through surface hardness test. **B** Acrylic palatal appliance preparation and intraoral phase. **C** After 14 days, enamel blocks and biofilm were collected from palatal appliance. **D** F, Ca, P and EPS content in biofilm analysis. **E** Surface hardness test after each phase. **F** Enamel blocks were sectioned longitudinally. **G** F, Ca and P content in enamel analysis. **H** Cross-sectional hardness test. 71

FIGURAS CAPÍTULO 4

- Figure 1 - **A** Enamel blocks selection through surface hardness test. **B** Enamel subsurface demineralization **C** Acrylic palatal appliance preparation and intraoral phase – in vivo dentifrice treatment. **D** After 3-days experiment, enamel blocks are removed from palatal appliance. **E** Surface hardness test after each phase. **F** Enamel blocks were sectioned longitudinally. **G** F, Ca and P content in enamel analysis. **H** Cross-sectional hardness test. 84

Figure 2 - Percentage of surface hardness recovery in enamel blocks following treatment with experimental groups. Means followed by distinct letters are significantly different. 85

LISTA DE TABELAS

TABELAS CAPÍTULO 1

Table 1 -	Integrated Mineral Loss (IML) values (means $\pm$ SD) calculated from the mineral content depth profiles.	46
-----------	---	----

TABELAS CAPÍTULO 2

Table 1 -	Lactic acid production (mean $\pm$ SD) and Colony Forming Unit (CFU counts) (mean $\pm$ SD) from experiment 2.	58
Table 2 -	Lactic acid production (mean $\pm$ SD) and Colony Forming Unit (CFU counts) (mean $\pm$ SD) from experiment 3.	58
Table 3 -	Lactic acid production (mean $\pm$ SD) and Colony Forming Unit (CFU counts) (mean $\pm$ SD) from experiment 4.	58

TABELAS CAPÍTULO 3

Table 1 -	Total fluoride (FT) and ionic fluoride (FI) concentrations (mean $\pm$ SD, n=3) in dentifrices.	72
Table 2 -	Fluoride (F), calcium (Ca) and phosphorus (P) concentration in enamel and percentage of changes in surface hardness (%SH) and integrated loss of subsurface hardness (Δ KHN) (mean $\pm$ SD) of the enamel blocks according to the treatments.	72
Table 3 -	Fluoride (F), calcium (Ca), phosphorus (P) and extracellular polysaccharides (EPS) concentration (means $\pm$ SD) in dental biofilm according to the treatments.	73

TABELAS CAPÍTULO 4

Table 1 -	Means ($\pm$ SD) of SH, SH ₁ , SH ₂ and percentage of surface hardness recovery (%SH _R) and integrated loss of subsurface area (Δ KHN) in enamel blocks according to the treatments.	86
-----------	---	----

Table 2 -	Means ($\pm$ SD) of integrated loss of subsurface area (Δ KHN) in enamel blocks according to the treatments.	86
Table 3 -	Means ($\pm$ SD) of fluoride (F), calcium (Ca) and phosphorus (P) in enamel blocks according to the treatments.	86

Sumário



SUMÁRIO

1.	Introdução Geral	31
2.	Capítulo 1 - <i>In vitro</i> evaluation of different fluoride concentration supplemented with trimetaphosphate on enamel de- and remineralization.	36
2.1.	Abstract	37
2.2.	Introduction	38
2.3.	Material and Methods	39
2.4.	Results	40
2.5.	Discussion	41
2.6.	References	42
3.	Capítulo 2 - Evaluation of trimetaphosphate effect on microcosm and single species biofilm <i>in vitro</i> .	47
3.1.	Abstract	48
3.2.	Introduction	49
3.3.	Material and Methods	49
3.4.	Results	52
3.5.	Discussion	53
3.6.	References	54
4.	Capítulo 3 - Effectiveness of a dentifrice with low fluoride content supplemented with trimetaphosphate on enamel demineralization <i>in situ</i> .	59
4.1.	Abstract	60
4.2.	Introduction	61
4.3.	Material and Methods	62
4.4.	Results	65
4.5.	Discussion	66
4.6.	References	68
5.	Capítulo 4 - Remineralizing potential of a dentifrice with low fluoride content supplemented with sodium trimetaphosphate - <i>in situ</i> study.	74
5.1.	Abstract	75
5.2.	Introduction	76
5.3.	Material and Methods	77
5.4.	Results	80

5.5. Discussion	80
5.6. References	82
6. Anexos	85

Introdução Geral



INTRODUÇÃO GERAL

A busca de meios para reduzir a cárie dentária tem sido um dos principais objetivos neste último século. A introdução do fluoreto (F) na década de 50, como principal agente de prevenção, causou uma redução em sua incidência. O sucesso obtido pela utilização do F levou sua adição não só na água de abastecimento público, como também em vários produtos de higiene bucal. O resultado acumulativo do uso excessivo levou ao aumento na incidência de fluorose dentária (Mascarenhas, 2000).

A utilização de dentifrícios fluoretados foi considerada uma das principais causas do aumento da fluorose dentária (Pendrys e Stamm, 1990; Mascarenhas, 2000). Observou-se em um estudo com crianças que viviam em áreas com água não fluoretada, mas que tinham acesso a dentifrícios fluoretados antes de 2 anos de idade, apresentavam fluorose dentária, sugerindo que o uso de dentifrícios antes dessa idade é um fator de significância para o desenvolvimento da fluorose dentária (Lalumandier, 1992). A recomendação do uso de dentifrícios fluoretados por crianças com menos de 6 anos de idade promove alto risco, pois nessa faixa etária o reflexo de expectoração ainda está em desenvolvimento, resultando em maior ingestão de dentifrício durante a escovação. Crianças com idade entre 1-3 anos ingerem entre 30-75% do dentifrício durante a escovação e crianças entre 4-7 anos, 14-48% (Warren e Levy, 1999). Apesar das propostas em diminuir a incidência de fluorose dentária através da escovação supervisionada, uso de quantidades reduzidas de dentifrício e redução do orifício da embalagem, a concentração de F acrescentada à maior parte dos dentifrícios comerciais infantis disponíveis no mercado é de 1100 µg F/g, semelhante aos dentifrícios utilizados por adultos. Embora se saiba que quanto maior a concentração de F, maior a sua efetividade, a utilização de altas concentrações de F não elimina o aparecimento de cárie dentária na população (Roberts, 1995).

Portanto, umas das maneiras para reduzir a ingestão de F pelas crianças seria a utilização de dentifrícios com menores concentrações desse íon (Horowitz, 1992, Tanever et al., 2006), porém dentifrícios com baixa concentração de F têm demonstrado ser menos efetivos que aqueles contendo 1000 µg F/g (Koch et al., 1982, Ammari et al., 2003). Uma das formas para aumentar sua efetividade seria a adição de agentes alternativos que proporcionem uma ação anticariogênica adicional

(Roberts, 1995; Zero, 2006). Entretanto, a combinação de F e outros suplementos deve ser realizada de maneira ponderada para evitar que o F torne-se indisponível.

A suplementação com sais de cálcio (Ca) e fosfato tem sido uma das alternativas para aumentar a efetividade do F. Embora o processo da remineralização seja intensificado pela presença do F, depende primariamente da disponibilidade desses íons na saliva (Schemehorn et al., 1999a,b). A presença desses íons no ambiente bucal durante o desafio cariogênico proporciona uma diminuição no processo de desmineralização e um aumento no processo de remineralização do esmalte dentário (ten Cate et al., 2000). O processo de remineralização pode ocorrer de duas maneiras: através da precipitação de fosfatos de cálcio ou pelo crescimento dos cristais de esmalte remanescentes através do Ca e P presentes na saliva (Ingram e Edgar, 1994). Entretanto, a concentração desses íons é limitada. A utilização de dentifrícios suplementados poderia aumentar a disponibilidade desses íons na saliva e ao mesmo tempo proporcionar reserva residual no biofilme, fluido da placa e no esmalte dentário, a partir da qual o F pode ser incorporado aos cristais minerais do esmalte ou se depositar como CaF_2 . A concentração desses íons, F, Ca e fosfato no biofilme bacteriano tem apresentado uma relação inversa na incidência de cárie (Shaw et al., 1983). Esses íons são liberados no fluido da placa causando uma redução na desmineralização e aumento da remineralização pela supersaturação em relação ao esmalte dentário (Tanaka & Margolis, 1999). A suplementação tem a função de suprir F como agente ativo e/ou cálcio e fosfato.

A associação de fosfatos à redução da cárie dentária teve início na década de 60 (Nizel e Harris, 1964; Harris et al., 1967; Henry and Navia, 1969; Gonzalez, 1971; Larson et al., 1972; Gonzalez et al., 1973; Städtler et al., 1996), quando foram adicionados em dietas (Harris et al., 1967; Henry & Navia, 1969; Larson et al., 1972), gomas de mascar (Finn et al., 1978, Vogel et al., 2000) e mais tarde em dentifrícios (Ständtler et al., 1996; O'Mullane et al., 1997; Takeshita et al. 2009). Dentre os vários sais de fosfato, o trimetafosfato de sódio (TMP) apresentou maior ação anticariogênica (Harris et al., 1967). Entretanto, seu mecanismo de ação ainda não está bem esclarecido (Roberts, 1995). Estudos sugerem que a ação do TMP pode estar relacionada com uma ação local (Harris et al., 1967, Henry and Navia, 1969), sendo adsorvido à superfície do esmalte (Gonzalez, 1971; Larson et al., 1972;

Gonzalez et al., 1973), causando uma redução na solubilidade da hidroxiapatita (Mcgaughey and Stowell, 1977) e reduzindo as trocas minerais entre o meio e o esmalte (Gonzalez, 1971; Gonzalez et al., 1973). Além disso, a ação local do TMP poderia influenciar a colonização dos microorganismos no biofilme (Henry and Navia, 1969) e a adesão de proteínas salivares (Briscoe and Pruitt, 1975). Um estudo clínico demonstrou uma alteração no biofilme dentário exposto ao TMP, ocorrendo uma diminuição dos *Streptococci* e aumento de *Veillonella* (Dennis et al., 1976). Por outro lado, outro estudo clínico observou que o TMP não altera a quantidade de biofilme formado nem sua composição microbiológica (Finn et al., 1978). Portanto, ainda há discussões controversas sobre o mecanismo de ação do TMP tanto sobre o esmalte como sobre o biofilme dentário.

A suplementação com TMP em dentifrícios teve início na década de 90. Trabalhos clínicos utilizando dentifrícios com 3% TMP não associado ao F mostraram uma ligeira redução nos incrementos de cárie quando comparados a um dentifrício placebo (Ständtler, 1996). Outro, porém, mostrou que a adição de 3% TMP a um dentifrício de 1500 µg F/g não mostrou diferenças significantes quando comparado ao mesmo dentifrício sem a suplementação (O'Mullane et al., 1997), indicando que na presença de altas concentrações de F a suplementação de TMP não traz um efeito adicional na ação anticariogênica. Entretanto, Takeshita et al. (2009) demonstraram, *in vitro*, que a suplementação com concentrações acima de 0,25% TMP em um dentifrício de reduzida concentração de F (500 µg/g) mostrou uma ação semelhante a um dentifrício padrão (1100 µg/g). A partir disso, levantou-se a hipótese pela qual é possível aumentar a ação anticariogênica de dentifrícios de baixa concentração de F através da suplementação com TMP.

A combinação de TMP e F no mesmo dentifrício tem demonstrado ser estável, entretanto, para atestar sua eficácia bem como validar novas formulações é necessário verificar sua capacidade em inibir a desmineralização e ativar a remineralização do esmalte (ADA, 1985). Um dos modelos *in vitro* utilizados na avaliação desses produtos é a ciclagem de pH que permite simular o desenvolvimento de cárie sob condições controladas (White, 1995). Em estudos *in situ* o modelo mais utilizado é o "teste intra-oral de cariogenicidade" (ITC), capaz de avaliar o efeito anticariogênico de produtos fluoretados com a presença de fatores interferentes como saliva e placa bacteriana (Zero, 1995). A análise de alguns

parâmetros como: incorporação de F pelo esmalte, progressão da lesão, desmineralização e remineralização do esmalte pode indicar a eficácia desses produtos (Faller, 1995). Ao contrário de estudos clínicos que necessitam de grande número amostral, uma das maiores vantagens dos modelos de estudo *in situ* é a utilização de pequeno número de voluntários (Featherstone e Zero, 1992).

A partir da utilização de diferentes modelos de estudo, tanto *in vitro* como *in situ*, o objetivo do presente trabalho foi avaliar a ação do TMP sobre o processo des-mineralização do esmalte, e sobre o biofilme formado *in vitro* e *in situ*, em associação ou não ao F, na tentativa de se obter mais informações sobre o mecanismo de ação em que estão envolvidos. Os trabalhos foram divididos em 4 capítulos, nos quais os capítulos 1 e 2 estão relacionados com os trabalhos *in vitro*, e os capítulos 3 e 4, com os trabalhos *in situ*.

Capítulo 1



2 Evaluation of different fluoride concentrations supplemented with trimetaphosphate on enamel de- and remineralization.*

2.1 ABSTRACT

Objective: The aim of this study was to evaluate the effects of TMP added to different concentrations of fluoride (F) on the de- and remineralization of enamel lesions.

Methods: Bovine enamel specimens were submitted to 15 days of pH-cycling with a daily schedule of 6 cycles, each 0.5 h demineralization and 2.5 h remineralization. The treatment was performed for 5 min in individual 5 mL aliquots of 30wt% dilutions of 0, 500, 1500 or 3000 µg F/g with or without the addition of 3% sodium trimetaphosphate (TMP). After the pH-cycling period the enamel specimens were analyzed by microradiography (TMR).

Results: The TMR data showed the formation of a second lesion (at depths beyond the original lesion) in the low F groups. This phenomenon, which might lead to lesion progression, was not found in the TMP groups, which also showed lower remineralization of the original lesions.

Conclusion: We conclude that TMP affects both de- and remineralization, resulting in different remineralization patterns inside the lesion.

Key words: pH cycling, fluoride, sodium trimetaphosphate, demineralization, remineralization.

*Capítulo escrito de acordo com as instruções do periódico Archives of Oral Biology (ANEXO B)

2.2 INTRODUCTION

The cariostatic effects of phosphate salts have been studied since the 1960s. Questions regarding the mode of action and efficacy of phosphates has led to numerous laboratory, animal and clinical studies comparing different compounds, such as ortho-, meta-, pyro- and poly-phosphates.^{1,2,3,4,5,6} Among all these phosphate salts, sodium trimetaphosphate (TMP) came out as the most effective anticaries agent, with an effectivity in rodents similar to fluoride.² While many studies were positive, most reports still question the precise mechanism of action of TMP.

Phosphate salts generally act as buffer at values around neutral pH. However, the effectiveness of TMP does not appear to be related to this characteristic: TMP is a ring structure which does not provide hydrogen ions for buffering. One of the proposed hypotheses regards its capacity to improve the stability of hydroxyapatite.⁷ Caries results from the selective mineral dissolution by low pK acids at the enamel surface and diffusion of acids through enamel porosities. TMP probably replaces phosphate groups and these stronger adsorbing groups protect the surface against dissolution during the caries attack,³ as it does at the crystallite level.

Most studies suggest a mode of action for TMP different from fluoride (F), and propose TMP as an alternative or additional agent which might even be synergistic with fluoride. Gonzalez et al.⁵ reported that when both agents were present during acid challenge a less soluble fluorapatite mineral was formed.

In spite of many *in vitro* studies demonstrating favorable F plus TMP results, the most recent clinical study involving TMP failed to show an overall additional effect when TMP was added to (1000 or 1500 µg F/g) fluoride toothpastes.⁸ Although it was not specifically discussed, this study did show reduced caries increments when TMP was added to a 1000 µg F/g. Similarly, Takeshita et al.⁹ reported an additional effect of TMP when it was added to a 500 µg F/g dentifrice, and studied in a pH-cycling study of initially sound enamel. They hypothesized that fluoride used at higher concentrations lead to a maximum in 'caries' inhibition, where favorable TMP effects cannot be separated.

Considering the above, this study aimed to further explore the effects of TMP added to a wide range of fluoride concentrations on enamel lesion de- and remineralization, and specifically focusing on the de/remineralization patterns inside the lesion.

2.3 MATERIALS AND METHODS

Experimental Design

Bovine enamel discs ($n = 45$) with artificial caries lesions were allocated in 8 groups ($n=5$) after a 3 day pH-cycling regime to determine baseline characteristics of the lesions. The calcium uptake and loss data were used to form groups with similar average de-/remineralization. The enamel specimens were then submitted to 15 days pH-cycling with daily treatments. Calcium was measured in the daily refreshed de- and remineralization solutions. After the pH-cycling period the enamel specimens were analyzed by microradiography and compared to the remaining 5 enamel lesions that were not used during the experimental period (baseline group).

Enamel Specimens and Lesion Formation

Enamel discs (22 mm^2 each) were cut from bovine incisors with a hollow drill and embedded in resin. The enamel specimens were ground flat to remove approximately $200\mu\text{m}$ surface enamel on 600 grit silicon carbide abrasive paper under running tap water. Lesions were formed in a methylcellulose gel and 0.1 mol/L lactate buffer system at $\text{pH } 4.6^{10,11}$ for 10 days.

pH-cycling

The experimental period involved 3 days of pre-cycling and 15 days pH-cycling with treatments. It was performed with a daily schedule of 6 cycles, each 0.5h demineralization ($1.5 \text{ mmol/L CaCl}_2$, $0.9 \text{ mmol/L KH}_2\text{PO}_4$, and 50 mmol/L acetate, $\text{pH } 4.6$, 3 mL aliquots/specimens) and 2.5h remineralization ($1.5 \text{ mmol/L CaCl}_2$, $0.9 \text{ mmol/L KH}_2\text{PO}_4$, 130 mmol/L KCl , and 20 mmol/L HEPES , $\text{pH } 7.0$, 3 mL aliquots/specimens), followed by a 'night' period of 6h remineralization. During the weekends, the specimens were kept in the remineralization solution at room temperature. The solutions were analyzed and refreshed daily.

Treatment Groups

Daily treatments were given after the six-hour remineralization 'night' period: Specimens were immersed for 5 min in individual 5 mL aliquots of 30wt% dilutions of 0, 500, 1500 or 3000 $\mu\text{g F/g}$ sodium fluoride (NaF , Merck, Germany) with or without 3% sodium trimetaphosphate (TMP, Sigma-Aldrich Co., USA) solutions in distilled

water. Fluoride contents were confirmed by gas chromatography (data not shown). Thirty percent dilutions were used for treatments, as is done in toothpaste studies. After treatment, the specimens were rinsed (in tap and distilled water) in a standardized way to remove excess treatment solution.

Transverse Microradiography

After the pH-cycling process, two 400µm sections were cut with a water-cooled diamond-coated wire saw (Well type 3242, Ebner, Mannheim, Germany). Sections were ground to 100µm thickness by means of 3µm Al₂O₃ particles (Logitech PM4, Glasgow, Scotland). Sections were microradiographed on high-resolution plates (K1A Photoplates, Microchrome Technology Products, San Jose, CA, USA) with soft (20 kV) X-rays, together with a reference stepwedge (13 steps, 0–300µm aluminum foil). Microradiograms were scanned with dedicated software (TMR software 1.25, Inspektor Research Systems, Amsterdam, The Netherlands), to produce the standard TMR output parameters: Mineral content versus depth profiles and Integrated Mineral Loss (IML).¹²

Statistics

For statistical analysis, GMC software¹³ was used and the significance limit was set at 5%. First, the normality and homogeneity of the samples was tested using Cochran test. Calcium data presented normal and homogeneous distribution and were submitted to two-way analysis of variance followed by Tukey's test. IML values were heterogeneous and were subjected to Kruskal-Wallis test, followed by Miller's test.

2.4 RESULTS

The microradiographs can be analyzed by the mineral depth profiles (Figure 1) and when the profiles are cumulated by the Integrated Mineral Loss (IML) values (Table 1). Water treatments resulted in an increase of the lesion depth and a lower mineral content in the lesion body (at a depth around 40µm). Together this resulted in an increase of IML of 676 vol%.µm. The mineral profiles show distinct differences when groups with the same fluoride levels with and without TMP are compared. In the original lesion (0-75µm) mineral content values are higher in the outer part of the

lesion (0-40µm) in the F-only groups, but at greater depth (40-75µm) the mineral content values are higher in the F+TMP groups. A general observation was also that in the F+TMP groups no second lesion was found in the originally sound enamel (beyond 75µm), this again was in contrast to the F only groups. In the low F group the second lesion was more evident than in high F concentrations. The cumulated IML data (Table 1) show that TMP addition to 500 and 1500 µg F/g resulted in significantly higher remineralization ($p<0.05$), while no significant differences were observed for the 3000 µg F/g groups with and without TMP.

2.5 DISCUSSION

The data show that TMP affects the processes of enamel de- and remineralization and also that the mode of action of TMP and fluoride in lesion de-/remineralization are different. As a consequence the remineralization patterns, in the depth of the remineralizing lesion, are different in the presence and absence of TMP.

The overall mineral loss (IML) showed that in presence of TMP the values were lower than in F only groups, mainly in 500 µg F/g group. The microradiographs revealed interesting findings. The mineral profiles are very different between the groups. The condition of pH-cycling with fluoride treatments gave a significant remineralization of the original lesion, but also the formation of a second lesion beyond the original lesion front, as has been observed previously.^{14,15} In contrast, in the TMP+F groups no second lesion was found and also the mineral profiles in the former lesion body were different. The TMP+F profiles showed significantly more remineralization close to the original lesion front. This suggests that this depth zone is favorably affected by a treatment involving TMP, as also evidenced by the lack of second lesion. But considering the outer part of the lesion (0-40µm) the remineralization was lower in TMP+F groups.

Explaining this, the data support that fluoride and TMP have different mode of action in the dynamics of enamel de- and remineralization. TMP is particularly effective in inhibiting demineralization. However, by binding to the crystallite surface, replacing orthophosphate ions, TMP hampers crystal growth and hence remineralization, similar to pyrophosphate. In this respect the current study with enamel lesions confirms earlier findings on surface enamel by Gonzalez³. The different remineralization patterns throughout the lesion can be explained with the

same phenomenon. As TMP inhibits remineralization in the outer parts of the lesion, and considering that ion diffusion is rate limiting in remineralization,¹⁶ there will be a greater calcium flux inside the lesions with enhanced remineralization in the deeper layers of the lesion. This precipitation will more effectively block lesion pores at the lesion front and thereby hinder acid diffusion to the underlying sound enamel (hence second lesion formation).

The pH-cycling approach provides an interesting method to simulate caries development under controlled conditions¹⁷ and mimic de- and remineralization process *in vitro*. In that sense it was originally developed to assess the effects of agents on dental hard tissues¹⁸ and has been used and modified extensively. The pH-cycling method, as used in this study, consists of a microradiographic assessment of the lesions after pH-cycling. In the current study, microradiography was instrumental to disclose how treatments modified the mineralization patterns throughout the lesion and how these were influenced by fluoride and particularly TMP treatments. We conclude that the findings reveal aspect of the working mechanism of TMP that were questioned by numerous authors since the 1960s.

Until today the formation of a second lesion occurring under the same conditions (and simultaneously) when preformed lesions remineralize has been a challenging observation. Although this was first observed in laboratory experiments, it parallels the findings *in vivo* of lesion progression underneath seemingly sound surfaces in the case of fluoride administration.¹⁹

Extrapolating our current findings to the clinical situation we conclude that the use of TMP could, under optimal conditions, prevent such undesirable lesion progression.

2.6 REFERENCES

1. Harris RS, Nizel AE, Walsh BN. The effect of phosphate structure on dental caries development in rats. *J Dent Res* 1967; 46:290-294.
2. Henry, C.A., Navia, J.M. Sodium trimetaphosphate influence on the early development of rat caries and concurrent microbial changes. *Caries Res* 1969; 3:326-338.
3. Gonzalez M. Effect of trimetaphosphate ions on the process of mineralization. *J Dent Res* 1971; 50:1056-1064.

4. Larson RH, Spalter CD, Clemmer BA, Scherp HW. Continuous versus intermittent feedings of different levels of trimetaphosphate in relation to caries development in the rat. *Arch Oral Biol* 1972; 17:1537-41.
5. Gonzalez M, Jeansonne BG, Feagin FF. Trimetaphosphate and fluoride actions on mineralization at the enamel-solution interface. *J Dent Res* 1973; 52:261-266.
6. Städtler P, Müller-Bruckschwaiger K, Schäfer F, Huntington E. The effect of sodium trimetaphosphate on caries: a 3-year clinical toothpaste trial. *Caries Res* 1996; 30:418-22.
7. McGaughey C, Stowell EC. Effects of polyphosphates on the solubility and mineralization of HA: relevance to a rationale for anticaries activity. *J Dent Res* 1977; 56:579-87.
8. O'Mullane DM, Kavanagh D, Ellwood RP, Chesters RK, Schafer F, Huntington E, Jones PR. A three-year clinical trial of a combination of trimetaphosphate and sodium fluoride in silica toothpastes. *J Dent Res* 1997; 76:1776-81.
9. Takeshita EM, Castro LP, Sasaki KT, Delbem, ACB. *In vitro* evaluation of dentifrice with low fluoride content supplemented with trimetaphosphate. *Caries Res* 2009; 43:50-56.
10. Ingram GS, Silvertone LM. A chemical and histological study of artificial caries in human dental enamel in vitro. *Caries Res* 1981; 15:393-398.
11. ten Cate JM, Dundon KA, Vernon PG, Damato FA, Huntington E, Exterkate RA, Wefel JS, Jordan T, Stephen KW, Roberts AJ. Preparation and measurement of artificial enamel lesion, a four-laboratory ring test. *Caries Res* 1996; 30:400-407.
12. Arends J, ten Bosch JJ. Demineralization and remineralization evaluation techniques. *J Dent Res* 1992; 71 Spec No:924-8.
13. Campos GM. GMC 2002. Ribeirão Preto: School of Dentistry, n.d. Available at: <http://www.forp.usp.br/restauradora/gmc/gmc.htm#gmc>. Accessed on feb 21, 2002.
14. ten Cate JM, Exterkate RAM, Buijs MJ. The relative efficacy of fluoride toothpastes assessed with pH cycling. *Caries Res* 2006; 40:136-141.
15. ten Cate JM, Buijs MJ, Chaussain Miller C, Exterkate RAM. Elevated fluoride products enhance remineralization of advanced enamel lesion. *J Dent Res* 2008; 87:943-947.
16. ten Cate JM, Arends J.; Remineralization of artificial enamel lesions in vitro. II. Determination of activation energy and reaction order. *Caries Res*. 1978; 12: 213-22.
17. White DJ. The application of in vitro models to research on demineralization and remineralization of the teeth. *Adv Dent Res* 1995; 9:175-93.

18. ten Cate JM, Duijsters PP. Alternating demineralization and remineralization of artificial enamel lesions. *Caries Res* 1982; 16:201-210.
19. Weerheijm KL, Kidd EA, Groen HJ. The effect of fluoridation on the occurrence of hidden caries in clinically sound occlusal surfaces. *Caries Res* 1997; 31:30-4.

Table

Table 1 – Integrated Mineral Loss (IML) values calculated from the mineral content depth profiles.

	IML (vol%.µm)
Baseline	3610 ± 257 ^a
Water- negative control	4286 ± 342 ^{a,b}
3% TMP	3397 ± 152 ^{b,c}
500ppm F	3035 ± 247 ^c
500ppm F 3% TMP	2677 ± 182 ^d
1500ppm F	2584 ± 232 ^d
1500ppm F 3% TMP	2290 ± 172 ^e
3000ppm F	2230 ± 256 ^e
3000ppm F 3% TMP	2213 ± 388 ^e

Means followed by distinct letters are significantly different. Kruskal-Wallis (p<0.001).

Figure

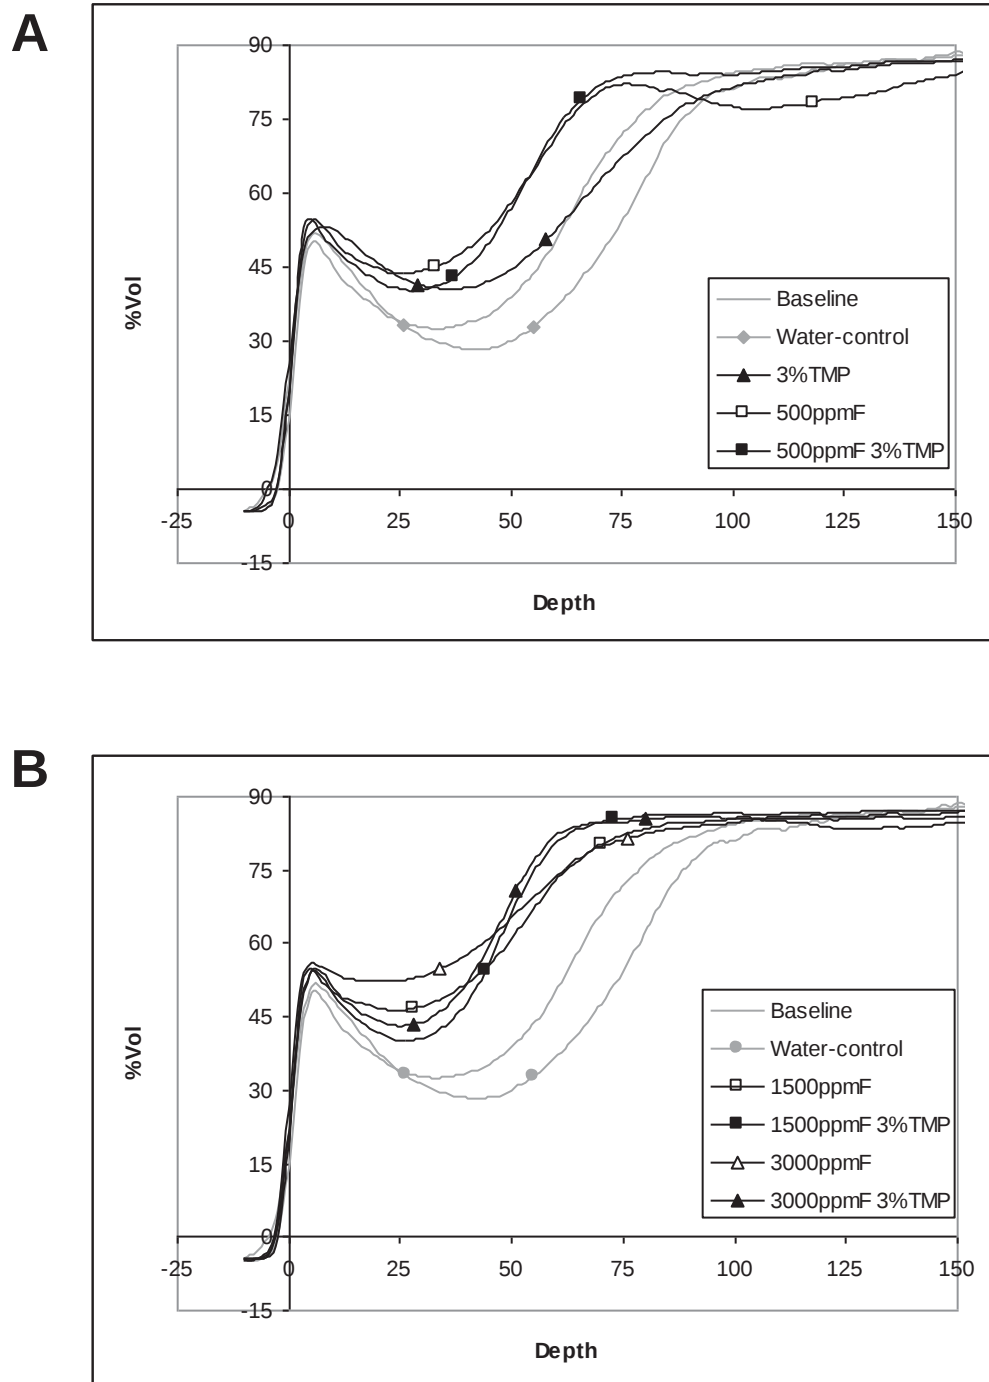


Figure 1 – Average mineral content profiles (vol% mineral versus depth) recorded from microradiographs taken from specimens of lower (Panel A) and higher fluoride groups (Panel B), both with and without TMP.

Capítulo 2



3 Evaluation of trimetaphosphate effect on microcosm and single species biofilm *in vitro*.*

3.1 ABSTRACT

Objective: Sodium trimetaphosphate (TMP) is considered the most effective anticaries agent among phosphates. The mode of action on hard tissues and biofilm is still unclear. New *in vitro* models have been developed to help explain how it could act. The aim of this study was to evaluate the effect of TMP on microcosm and single species biofilm formed in an *in vitro* biofilm model and its efficacy when combined to different antimicrobials.

Methods: This study was carried out in three experiments. In experiment 1 (microcosm biofilm), glass and enamel were used as substrata. The treatment groups were control, sterile solution with 3% TMP pre-treatment and treatment after 8 hours *in vitro* biofilm formation. In experiment 2 (single species biofilm), only glass samples were used as substratum. The treatment groups were control, sterile solution with 1% TMP and 0.11% NaF solution with or without 1% TMP. And in experiment 3 (single species biofilm), glass samples were used as substratum. The treatment was done with combination of TMP and antimicrobials solutions. For all experiments, effect on biofilm was analyzed by Colony Forming Unit (CFU) counts and lactic acid production.

Results: The results showed that in both microcosm and single species biofilm TMP did not alter lactic acid production and CFU counts. And the combination of TMP to others antimicrobials did bring an additional effect on reducing acid production and CFU counts.

Conclusion: We can conclude that in the present study TMP had no action on biofilm.

Key words: antimicrobials, sodium trimetaphosphate, biofilm, microcosm biofilm, *S. mutans*.

*Capítulo escrito de acordo com as instruções do periódico Archives of Oral Biology (ANEXO B)

3.2 INTRODUCTION

It is well established that dental caries is a multifactorial disease in which the fermentation of food sugars by bacteria from the biofilm can lead to tooth surface demineralization. Antimicrobial agents have been studied to modify the biofilm to reduce the cariogenic challenge. Nowadays, biofilm models have been developed to simulate plaque activities *in vitro* and to test antimicrobials effect on biofilm.^{1,2,3,4,5}

After 60 decades, fluoride (F) has become the most important agent to reduce dental caries. However, the widespread use has been related to dental fluorosis in some countries. For that reason, developing effective alternative agents would make caries prevention less dependent on fluoride.⁶

Phosphate salts have been considered alternative anticaries agent.^{7,8} Harris et al.⁹ demonstrated that sodium trimetaphosphate (TMP) is the most effective phosphate salt against dental caries. Studies carried out in the past demonstrated the affinity of TMP on enamel surface and/or hydroxyapatite resulting in a reduction of enamel solubility.^{10,11,12} A recent study¹³ showed an additional effect of TMP in prevent enamel demineralization when added to dentifrice with low F concentration.

However, there is a lack of information about phosphates action against oral bacteria. Generally, they are used as food additives to inhibit bacterial growth.¹⁴ It is suggested that antibacterial action of some condensed phosphate is related to their chelating capacity.¹⁵ However, regarding TMP literature is controversial. TMP is a cyclic phosphate and in terms of mechanism of action is different from others phosphate compounds. Since TMP has affinity to enamel surface, a new biofilm model developed by Exterkate et al.⁵ was suitable to attest TMP action on biofilm formed on different substrates. This way, the aim of this study was to verify the effect of TMP on biofilm and its efficacy when combined to different antimicrobials.

3.3 MATERIAL AND METHODS

Experimental design

The present study was carried out in three experiments:

Experiment 1: enamel and glass samples were used as substratum to grow *in vitro* biofilm. The treatment groups were control, sterile solution with 3% TMP pre-treatment and treatment after 8 hours *in vitro* biofilm formation.

Experiment 2: glass samples were used as substratum. The treatment groups were control, sterile solution with 1% TMP and 0.11% NaF solution with or without 1% TMP.

Experiment 3: glass samples were used as substratum. The treatment groups were control, sterile solution with 1% TMP and chlorhexidine 0.05 and 0.1% solution with or without 1% TMP.

Experiment 4: glass samples were used as substratum. The treatment groups were control, sterile solution with 1% TMP and cetylpyridinium chloride 0.05 and 0.1% solution with or without 1% TMP.

For all experiments, effect on biofilm was analyzed by Colony Forming Unit (CFU) counts and lactic acid production.

Microcosm Biofilm growth conditions and harvesting

A growth medium was used as described by McBain et al.¹⁶, which contained mucin (type II, porcine, gastric), 2.5 g/L; bacteriological peptone, 2.0 g/L; tryptone, 2.0 g/L; yeast extract, 1.0 g/L; NaCl, 0.35 g/L; KCl, 0.2 g/L; CaCl₂, 0.2 g/L; cysteine hydrochloride, 0.1 g/L; haemin, 0.001 g/L; vitamin K₁, 0.0002 g/L, pH 7. The biofilm model used is described by Exterkate et al.⁵. Sterilized glass or enamel discs were used as substrata that were positioned vertically in the wells of polystyrene, 24-well flat-bottomed microtiter plates. Each well was filled with 1.5 mL of growth medium with 0.2% (v/v) sucrose supplement. As inoculum a sample (400 µL) saliva-glycerol stock was added and the plate was incubated anaerobically at 37 °C (80% N₂, 10% CO₂ and 10% H₂). The medium was refreshed after 8, 16 and 24 h.

After growth the enamel and glass discs were removed from the wells, put into tubes with 2 mL of cysteine peptone water (CPW) (8.5 g NaCl, 5 g Bacto yeast extract, 1 g Bacto peptone, 0.5 g cysteine HCl per liter, pH 7.3) and dispersed by sonication on ice for 2 min at an amplitude of 40W (Vibra cell™, Sonics & Materials INC, USA). Serially diluted samples were plated onto TSA blood agar and incubated anaerobically at 37 °C for 72 h. The viability of cells grown in biofilms was determined by CFU counts.

Single species biofilm growth conditions and harvesting

S. mutans C180-2 kept at -80°C in 60% w/v glycerol was incubated overnight on brain heart infusion (BHI) and grown at 37°C anaerobically (80% N_2 , 10% CO_2 and 10% H_2). 10 fold diluted overnight culture in half-strength BHI supplemented with 50 mM PIPES (medium) was inoculated anaerobically at 37°C in 24-well flat-bottomed microtiter plates (bio-one; Greiner, Frickenhausen, Germany). The biofilm model used is described by Exterkate et al.⁵. After 8 h the medium was refreshed and the biofilm incubated anaerobically for an additional 16 h.

After growth the glass discs were removed from the wells, put into tubes with 2 mL of CPW and dispersed by sonication on ice for 2 min at an amplitude of 40W (Vibra cell™, Sonics & Materials INC, USA). Serially diluted samples were plated onto BHI agar and incubated anaerobically at 37°C for 72 h. The viability of cells grown in biofilms was determined by CFU counts

Treatments

Experiment – 1: A sterile solution of TMP 3% (Sigma, St Louis, MO, USA) was freshly prepared on the day of use. The treatment was carried out during 1 hour according to the experimental design.

Experiment – 2: Sterile solutions with TMP 1% and 0.11% sodium fluoride (NaF, Merck, Germany) and one solution containing both were freshly prepared on the day of use. The samples were stored overnight in treatment solutions, before starting incubation. Following, the treatments were carried out between fresh medium changes during 5 minutes.

Experiment – 3: Sterile solution of chlorhexidine, 0.05% and 0.1%, with or without 1% TMP was freshly prepared on the day of use. The treatment was carried out at the end of 24h biofilm growth.

Experiment – 4: Sterile solution of cetylpyridinium chloride, 0.05% and 0.1%, with or without 1% TMP was freshly prepared on the day of use. The treatment was carried out at the end of 24h biofilm growth.

Lactic acid production

After 24h and 48h, the samples were immediately placed on a 24-well plate containing PBW with 0.2% sucrose. The plate was incubated anaerobically for 3 hrs at 37° C. After that, the PBW was transferred into microtubes and placed in a water bath at 80°C for 5 min, to stop all acid production. The samples were stored at -20 °C for lactic acid estimations. The concentration of lactic acid was measured with an enzymatic–spectrophotometric method. The principle of the method is based on the enzymatic conversion of L-lactate to pyruvate with concomitant conversion of NAD⁺ to NADH, the increase in absorbance at 340 nm being proportional to NADH formation.

Statistics

For statistical analysis, GMC software¹⁷ was used and the significance limit was set at 5%. First, the normal distribution of the data and the homogeneity of the variances were tested using, respectively, the Kolmogorov-Smirnov and Cochran tests. The lactic acid data from experiment 1, 2 and 3 and CFU data from experiment 1 were heterogeneous and were subjected to Kruskal-Wallis test, followed by Miller's test. The lactic acid data from experiment 4 were subjected to ANOVA, followed by Tukey test. The CFU data of the experiment 2, 3 and 4 were log transformed and were subjected to ANOVA, followed by Tukey test.

3.4 RESULTS

Lactic acid production

The lactic acid production data are shown in figure 1 and table 1 to 3. In experiment 1, different substrata and treatments were compared. Both glass and enamel substrata showed similar behavior to TMP treatments. There were no differences between the two treatment groups and the control ($p < 0.05$). In experiment 2, there were no differences among the groups ($p > 0.05$). In experiment 3 and 4, CHX and CPC were effective in reduce acid production, but the combination with TMP did not bring an additional effect in both concentration.

Microorganism Growth on biofilm

The CFU counts are shown in table 1 to 4. In experiment 1, the treatment with TMP 3% did not induce decrease in CFU counts in microcosm biofilm. Even when TMP

treatments were carried out during overnight period before starting the experiment and at every change of medium no differences were found when compared to the control group (data not shown). Since experiment 1 showed no differences between the substrata, only glass discs were used in experiment 2 to 4. In experiment 2, NaF decreased *S. mutans* growth when compared to control group ($p < 0.05$), but the addition of TMP did not interfere on it ($p > 0.05$). In experiment 3, the results from chlorhexidine and cetylpyridinium chloride showed effective on reducing *S. mutans*. In both experiment TMP did not reduce total CFUs after biofilm established on substratum surface, since it was done after 24h. In both antimicrobials, TMP caused an increase of microorganism growth.

3.5 DISCUSSION

The data presented in this study demonstrated that the biofilm model used was suitable to grow biofilm on different substratum both in microcosm and single species biofilm. The model allows for the evaluation of antimicrobials agent, and TMP, on biofilm survival and metabolism.

Nowadays, the search for alternative anticaries agent has been increased to make caries prevention less dependent on fluoride. TMP is one of them but the mode of action remains unclear. Studies suggested in the past that TMP had local action that could influence the colonization of microorganisms responsible for dental caries¹⁸ and the binding of TMP to the enamel surface could inhibit proteins such as phosphatase, or perhaps cariogenic microorganisms and then they would be no longer available for enamel destruction.¹⁹

In a clinical study TMP had significant alterations in human plaque components. After TMP exposure numbers of total *streptococci* decreased and *Veillonella* increased. However, *S. mutans* did not alter.²⁰ Other clinical study observed that TMP did not alter either the amount of plaque formed or its microbiological composition.²¹

Since *in vitro* and *in vivo* studies remained controversial, in the present study the use of a new *in vitro* biofilm model played an important role to show that TMP in two tested concentrations, 1 and 3%, did not interfere on biofilm composition. When TMP was added to antimicrobials no positive effect was observed, TMP caused an increase of microorganism growth. Even literature suggested that TMP adsorbed to

enamel inhibits the binding of proteins to enamel surface, in the present study we observed that treatment of TMP on enamel surface did not avoid biofilm growth. In single species biofilm experiment *S. mutans* did not change comparing TMP and control group. And regarding microcosm biofilm the results are in agreement to that of Finn et al.²¹.

Therefore, the development of new biofilm models has made possible new studies evaluating the action of antibacterial agents on biofilm formed *in vitro*. The results from the present study can contribute to the discussion about TMP outcome from *in vitro* and *in vivo* studies by some authors.^{7,8} Although *in vivo* results are more remarkable, *in vitro* studies play an important role as well. The biofilm model used in this study based on Exterkate et al.⁵ was suitable to attest TMP influence on biofilm in different substrata. Therefore, we can conclude that in the present study TMP alone or combined to antimicrobials had no direct action on biofilm.

3.6 REFERENCES

1. Deng DM, van Loveren C, ten Cate JM. Caries-prevent induce remineralization of dentin in a biofilm model. *Caries Res* 2005; 39:216-223.
2. Kara D, Luppens SBI, ten Cate JM. Differences between single and dual-species biofilms of *Streptococcus mutans* and *Veillonella parvula* in growth, acidogenicity and susceptibility to chlorhexidine. *Eur J Oral Sci* 2006; 114:58-63.
3. Luppens SBI, Kara D, Bandounas L, Jonker MJ, Wittink FRA, Bruning O, Breit TM, ten Cate JM, Crielaard W. Effect of *Veillonella parvula* on the antimicrobial resistance and gene expression of *Streptococcus mutans* Brown in a dual-species biofilm. *Oral Microbiol Immunol* 2008; 23:183-189.
4. Deng DM, Hoogenkamp MA, Exterkate RAM, Jiang LM, van der Sluis LWM, ten Cate JM, Crielaard W. Influence of *Streptococcus mutans* and *Enterococcus faecalis* biofilm formation. *J Endod* 2009; 35:1249-1252.
5. Exterkate RAM, Crielaard W, ten Cate JM. Different Response to Amine Fluoride by *Streptococcus mutans* and Polymicrobial Biofilms in a Novel High-Throughput Active Attachment Model. *Caries Res* 2010; 44:372-379.
6. ten Cate JM. The need for antibacterial approaches to improve caries control. *Adv Dent Res* 2009; 21:8-12.
7. Ingram GS, Edgar WM. Interaction of fluoride and non-fluoride agents with the caries process. *Adv Dent Res* 1994; 8:158-165.

8. Roberts AJ. Role of models in assessing new agents for caries prevention--non-fluoride systems. *Adv Dent Res* 1995; 9:304-11.
9. Harris RS, Nizel AE, Walsh BN. The effect of phosphate structure on dental caries development in rats. *J Dent Res* 1967; 46:290-294.
10. McGaughey C, Stowell EC. Effects of polyphosphates on the solubility and mineralization of HA: relevance to a rationale for anticaries activity. *J Dent Res* 1977; 56:579-87.
11. Gonzalez M. Effect of trimetaphosphate ions on the process of mineralization. *J Dent Res* 1971; 50:1056-1064.
12. Gonzalez M, Jeanson BG, Feagin FF. Trimetaphosphate and fluoride actions on mineralization at the enamel-solution interface. *J Dent Res* 1973; 52:261-266.
13. Takeshita EM, Castro LP, Sasaki KT, Delbem, ACB. *In vitro* evaluation of dentifrice with low fluoride content supplemented with trimetaphosphate. *Caries Res* 2009; 43:50-56.
14. Hargreaves LL, Wood JM, Jarvis B. The antimicrobial effect of phosphates with particular reference to food products. British Food Manufacturing Industries Research association. *Scientific and Technical Surveys* 1972; 76:5.
15. Shibata H, Morioka T. Antibacterial action of condensed phosphates on the bacterium *streptococcus mutans* and experimental caries in the hamster. *Arch oral Biol* 1982; 27:809-816.
16. McBain AJ, Sissons C, Ledger RG, Sreenivasan PK, De Vizio W, Gilbert P. Development and characterization of a simple perfused oral microcosm. *J Appl Microbiol* 2005; 98:624-634.
17. Campos GM. GMC 2002. Ribeirão Preto: School of Dentistry, n.d. Available at: <http://www.forp.usp.br/restauradora/gmc/gmc.htm#gmc>. Accessed on feb 21, 2002.
18. Henry CA, Navia JM. Sodium trimetaphosphate influence on the early development of rat caries and concurrent microbial changes. *Caries Res* 1969; 3:326-338.
19. Briscoe JM, Pruitt KM. Comparison of the effect of linear and cyclic phosphate on the absorption of proteins by human enamel. *J Dent Res* 1975; 54:504-507.
20. Dennis DA, Gawronski TH, Cressey DE, Folke LEA. Effects of sodium trimetaphosphate supplementation of a high sucrose diet on the microbial and biochemical composition of four-day plaque and urine calcium and phosphorus levels. *J Dent Res* 1976; 55:787-196.

21. Finn SB, Frew RA, Leibowitz R, Morse W, Manson-Hing L, Brunelle J. The effect of sodium trimetaphosphate (TMP) as a chewing gum additive on caries increments in children. *J Am Dent Assoc* 1978; 96:651-655.

Figure

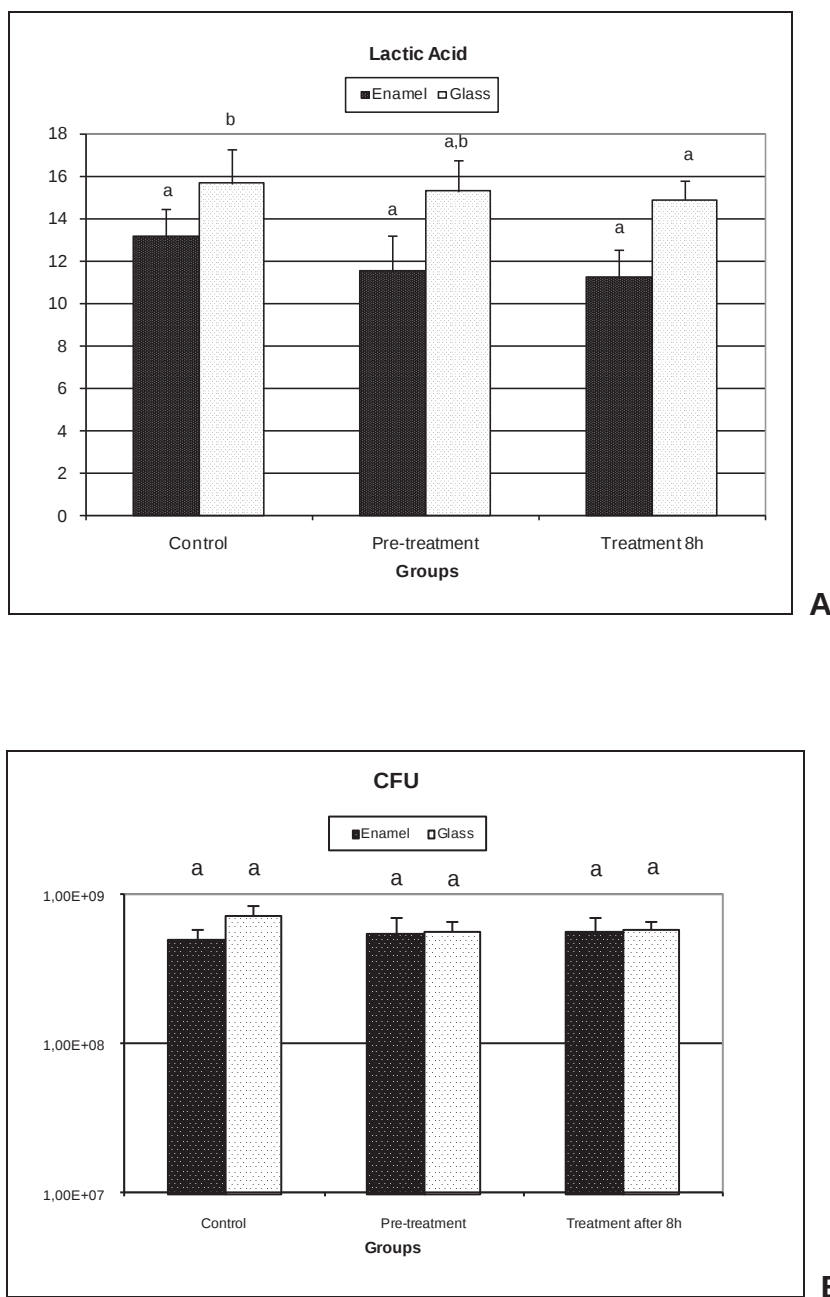


Figure 1 – Lactic acid data (mmol/L) (A) (mean $\pm$ SD) and Colony Forming Unit (CFU counts) (B) (mean $\pm$ SD) from experiment 1. Distinct letters indicate statistical significance ($p < 0.05$).

Tables

Table 1 - Lactic acid production (mean $\pm$ SD) and Colony Forming Unit (CFU) counts (mean $\pm$ SD) from experiment 2.

	Treatments			
	Control	TMP 1%	NaF 0.11%	NaF 0.11% TMP 1%
Lactic Acid	26.4 $\pm$ 2.6 ^a	29.1 $\pm$ 1.6 ^a	24 $\pm$ 3.5 ^a	23.5 $\pm$ 3.6 ^a
CFU (10 ⁸)	49.5 $\pm$ 3.4 ^a	44.4 $\pm$ 1.6 ^a	36.8 $\pm$ 3.4 ^b	36.4 $\pm$ 2.3 ^b

Within rows, distinct superscript letters indicate statistical significance ($p < 0.05$).

Table 2 - Lactic acid production (mean $\pm$ SD) and Colony Forming Unit (CFU) counts (mean $\pm$ SD) from experiment 3.

	Treatments				
	Control	CHX 0.05%	CHX 0.05% TMP 1%	CHX 0.1%	CHX 0.1% TMP 1%
Lactic Acid	27.2 $\pm$ 0.5 ^a	11.7 $\pm$ 0.8 ^b	18.5 $\pm$ 0.4 ^c	7.9 $\pm$ 1.2 ^d	11 $\pm$ 0.8 ^b
CFU (10 ⁸)	9.1 $\pm$ 1.8 ^a	2.6 $\pm$ 1.0 ^{b,c}	4.7 $\pm$ 3.3 ^c	0.8 $\pm$ 0.0 ^b	1.5 $\pm$ 0.8 ^c

Within rows, distinct superscript letters indicate statistical significance ($p < 0.05$).

Table 3 - Lactic acid production (mean $\pm$ SD) and Colony Forming Unit (CFU) counts (mean $\pm$ SD) from experiment 4.

	Treatments				
	Control	CPC 0.05%	CPC 0.05% TMP 1%	CPC 0.1%	CPC 0.1% TMP 1%
Lactic Acid	27 $\pm$ 1.8 ^a	11.5 $\pm$ 2.8 ^{a,b,d}	12.5 $\pm$ 0.2 ^b	8.7 $\pm$ 1.5 ^{c,d}	9.1 $\pm$ 1.5 ^d
CFU (10 ⁸)	3.9 $\pm$ 1.5 ^a	0.9 $\pm$ 0.2 ^b	0.8 $\pm$ 0.2 ^b	1.2 $\pm$ 0.5 ^b	1.0 $\pm$ 0.1 ^b

Within rows, distinct superscript letters indicate statistical significance ($p < 0.05$) indicate statistical significance (ANOVA, Bonferroni; $p < 0.001$).

Capítulo 3



4. Effectiveness of a dentifrice with low fluoride content supplemented with trimetaphosphate on enamel demineralization *in situ*.*

4.1 ABSTRACT

Objective: This study evaluate whether the supplementation with sodium trimetaphosphate (TMP) of a dentifrice with low fluoride (F) content (500 µg/g) would provide similar effect to that of a standard dentifrice (1100 µg F/g).

Methods: In this crossover double-blind study, 10 volunteers wore acrylic palatal appliance containing four enamel bovine blocks selected through surface hardness. The enamel blocks (n=160) were allocated to four treatment groups: placebo, dentifrice with 500 µg F/g, dentifrice with 500 µg F/g TMP 1% and dentifrice with 1100 µg F/g. Dentifrices treatment was performed 2x/day, and 20% sucrose solution was applied 6x/day. After each experimental period, the biofilm was collected for F, calcium (Ca), phosphorus (P) and insoluble extracellular polysaccharides (EPS) analysis. In each enamel block, Ca, F and P content was determined and surface hardness (SH₂) was again assessed to calculate the percentage change of surface hardness (%SH) and cross section hardness test was performed to calculate the integrated loss of subsurface area (ΔKHN). The data of dental biofilm analysis were homogeneous and were submitted to ANOVA, followed by Bonferroni test. Enamel data were heterogeneous and were subjected to Kruskal-Wallis test, followed by Miller's test.

Results: The results showed that the dentifrice with 500 µg F/g TMP 1% showed the lowest percentage change of surface hardness (p<0.05). Regarding F and Ca in enamel and biofilm there were no differences between dentifrice with 500F TMP 1% and positive control (p>0.05), but they were different when compared to dentifrice with 500 F (p<0.05).

Conclusion: It is concluded that the dentifrice with 500 µg F/g supplemented with TMP 1% had similar effect when compared to a standard dentifrice in an *in situ* model.

Keywords: dentifrice, fluoride, trimetaphosphate, dental enamel, *in situ*, demineralization, biofilm.

*Capítulo escrito de acordo com as instruções do periódico Archives of Oral Biology (ANEXO B)

4.1 INTRODUCTION

Recently, the use of fluoridated products has led to a decline in the prevalence dental caries. However, the widespread use of fluoride has caused an increase of dental fluorosis.^{1,2} The reduction of F concentration in dentifrices would be one of the possibilities to reduce the F ingestion by children under 6 years old.³ However, dentifrices with low F concentration (e.g. 500 µg F/g) have shown to be less effective than dentifrices with 1100 µg F/g dentifrice.^{4,5}

One method that can be used to increase the effectiveness of F dentifrices is by supplementing them with calcium and/or phosphate. In 60 decades, studies have demonstrated that some phosphate (P) salts have an anticariogenic activity.^{6,7} Sodium trimetaphosphate (TMP) seems to be the most effective against dental caries (6); however, the mechanism of action remains unclear.⁸ Studies suggest that TMP is adsorbed to the enamel surface, thereby reducing enamel demineralization,^{7, 9, 10} hydroxyapatite solubility,¹¹ mineral exchange, and changing the affinity between the enamel surface and salivary proteins.¹²

In clinical studies, a decrease of caries was observed after the addition of 1.5% and 3 % TMP in gum and dentifrice, respectively.^{13,14} However, it seems that TMP does not bring an additional effect in reducing caries when added to high fluoride dentifrices (1000 and 1500 µg F/g).¹⁵

On the other hand, Takeshita et al.¹⁶ showed that the addition of TMP in low F dentifrices resulted in a similar effectiveness to that of a standard dentifrice (1100 µg F/g) in an *in vitro* study. Those authors showed that, at concentrations above 1%, TMP increased surface hardness, Ca and F content in enamel treated with low F dentifrices.

Since the previous study¹⁶ was carried out using a pH cycling model that has some limitations in predicting clinical effectiveness,⁸ those results should not be considered definitive. In situ models have been used to evaluate fluoride containing dental products¹⁷ and may be considered as an intermediate stage between *in vivo* and *in vitro* studies, allowing the control of clinical conditions related to the development of caries.^{18,19} Considering the lack of information about the effects on enamel and biofilm of dentifrices with low F concentration supplemented with TMP, the aim was to evaluate whether the supplementation with sodium trimetaphosphate

(TMP) of a dentifrice with low-F content (500 µg/g) would provide similar effect to that of a standard dentifrice (1100 µg F/g).

4.2 MATERIAL AND METHODS

Experimental Design

This study was previously approved by the Human Research Ethical Committee (protocol#2007/01367) and all participants read and signed informed consent statements prior to study initiation. The experimental design is presented in figure 1. This crossover double blind study was performed in four phases of 14 days each. Ten volunteers wore acrylic palatal appliances with enamel bovine teeth that were previously stored in 2% formaldehyde solution (pH 7) for 30 days at room temperature.²⁰ Sound enamel blocks (4x4 mm, n=160) were sequentially polished and selected using a surface hardness test (SH) (330.0 up to 370.0 KHN). Then, the specimens were allocated to four treatments: placebo (negative control), dentifrice with 500 µg F/g, dentifrice with 500 µg F/g TMP 1% and a dentifrice with 1100 µg F/g (positive control). The cariogenic challenge was produced by dripping a 20% sucrose solution 6x/day. Dentifrices treatments were carried out 2x/day. After each experimental period, the biofilm was collected for F, calcium (Ca), phosphorus (Pi) and insoluble extracellular polysaccharides (EPS) analysis. The enamel surface hardness (SH₂) was again assessed to calculate the percentage change of surface hardness (%SH). The blocks were sectioned longitudinally and one of the halves underwent a cross-section hardness test to calculate the integrated loss of subsurface area (ΔKHN) while the other one had the F, Ca and Pi content in enamel determined.

Dentifrice formulation and Fluoride and Phosphorus Assessment

The experimental dentifrices were prepared in a laboratory and had the following ingredients: carboxymethylcellulose, sodium methyl-p-hydroxybenzoate, sodium saccharin, peppermint oil, glycerol, hydrated silica, sodium lauryl sulfate and water. Fluoride (NaF, Merck, Germany) concentration in experimental dentifrice was 500 µg F/g and it had 1% sodium trimetaphosphate (TMP, Sigma-Aldrich Co., St. Louis, MO, USA) added. A dentifrice without F and P (placebo, negative control) and one with 500 µg F/g and other with 1100 µg F/g (Crest™, Proctor & Gamble, USA, positive control) were also used. To ensure the F and Pi concentrations in the experimental

dentifrices, F in dentifrices was determined using a specific electrode for F ion (9609 BN – Orion Research Inc, Beverly, MA, USA) attached to an ion analyzer (Orion 720 A+ - Orion Research Inc), which was calibrated with standards containing 0.125 to 2.000 µg F/g. Pi concentration, and measured the levels of F according to the colorimetric method as described by Fiske and Subbarow,²¹ after being submitted to a previous acid hydrolysis.

Palatal appliance preparation and treatments

The oral appliances were prepared in acrylic resin (Jet - Articles Classic Odontológico, São Paulo, Brazil) in accordance with Hara et al.²². Four enamel blocks were fixed in the intraoral device in each phase. In order to allow accumulation of biofilm on the enamel blocks, a piece of gauze was fixed to the acrylic appliance leaving a space (1 mm) from the block surface.²³ To provide the cariogenic challenge, the volunteers were instructed to remove the device and drip 20% sucrose solution on each enamel block 6x/day. Five min later, the device was re-inserted into the mouth. The treatments with dentifrices were performed 2x/day, during the volunteers' habitual oral hygiene routine. The device was removed and dentifrice slurries (1:3 w/w) were dripped onto the blocks. The device was then washed in deionized water and re-inserted in the mouth. During the 7-day pre-experimental period and washout periods (7-days between each phase), the volunteers brushed their teeth with non-fluoridated dentifrices. The volunteers received all the instructions prior to the experimental procedures.

Microhardness Analysis

The enamel surface hardness was determined before (SH₁) and after each phase (SH₂) in each specimen using a Shimadzu HMV-2000 microhardness tester (Shimadzu Corp., Kyoto, Japan) under a 25g load for 10s. Five indentations, spaced 100 µm from each other, were made in the center of the enamel block. After each phase, five indentations were made spaced 100 µm from the baseline indentations. The percentage change of surface hardness (%SH) was calculated ($\%SH = 100 (SH_2 - SH_1)/SH_1$).

For the cross-sectional hardness measurements, the enamel blocks were longitudinally sectioned through their center and embedded in acrylic resin with the

cut face exposed and gradually polished. Three sequences of eight indentations at different distances (10, 30, 50, 70, 90, 110, 220 and 330 μm) were made from the surface of the enamel in the central region spaced 100 μm from each other, under a 25g load for 10s. The means were calculated for each distance and the integrated area (KHN x μm) of sound enamel and after each treatment was calculated up to a depth of 90 μm to calculate ΔKHN , through trapezoid rule: $\Delta\text{KHN} = \Delta X \cdot (Y1 + Y2) / 2$ (GraphPad Prism, version 3.02). Lesion depth was measured from the enamel surface up to the distance where hardness represented 95% of the value for sound enamel.

Fluoride, Calcium, and Phosphorus in Enamel

Enamel biopsy was performed according to the study by Weatherell et al.²⁴ Blocks measuring 2X2mm were obtained from one of the halves of the longitudinally sectioned blocks. The blocks were fixed to a mandrel and fixed to the top of a modified microscope. Self-adhesive polishing discs (13 mm of diameter) of 400 grit silicon carbide (BUEHLER) were fixed to the bottom of polystyrene crystal tubes (J-10, Injeplast, Sao Paulo, SP, Brazil). A layer of 50 μm deep of each enamel block was removed and 8 mL HCl 0.5 mol/L was added to the enamel powder. The tubes were kept under agitation for 15 minutes and 0.8 mL NaOH 0.5 mol/L was then added. For F analysis, the specific electrode for the Orion 9690 connected to an ion analyzer (Orion 720⁺) and TISAB II (total ionic strength adjustment buffer) at 1:1 ratio (TISAB:sample) were used. For Ca analysis, the cresolftalein colorimetric method (Katal, Belo Horizonte, MG, Brazil) was used. The Pi was measured according to Fiske and Subbarow.²¹

Analysis of Dental Biofilm Composition

After each experimental period, the biofilm formed on the enamel surface from each slab was collected and stored in microcentrifuge tubes. The biofilm samples were dried under vacuum with phosphorus pentoxide for 12 h at room temperature. Hydrochloric acid (0.5 mol/L) was added to the tubes in the proportion of 250 μL /mg plaque wet weight. After extraction for 3 h at room temperature under constant agitation, the same volume NaOH 0.5 mol/L was added. The samples were then centrifuged (11,000g) for 1 min and the supernatant retained for F, Ca and Pi

determination. EPS were extracted by adding NaOH 1.0 mol/L (10 µL/mg dry weight) to the biofilm. The samples were vortex for 1 min and after 3 h under agitation at room temperature they were centrifuged (1 min, 11.000g at room temperature).²⁵ EPS were precipitated from supernatants with 75% ethanol overnight, centrifuged and re-suspended in 1.0 mol/L NaOH.²⁶ EPS were determined by the phenol-sulfuric acid method.²⁷ The results were expressed as µg/mg dry weight.

Statistical Analysis

For statistical analysis, GMC software²⁸ was used and the significance limit was set at 5%. First, the normal distribution of the data and the homogeneity of the variances were tested using, respectively, the Kolmogorov-Smirnov and Cochran tests. The data of the dental biofilm analysis (F, Ca, Pi and IP) were normal and homogeneous and were submitted to ANOVA, followed by Bonferroni test. The variable Ca and IP were homogeneous after log transformation. Enamel data (%SH, ΔKHN, F, Ca and Pi) were heterogeneous and were subjected to Kruskal-Wallis test, followed by Miller's test.

4.3 RESULTS

The analysis of F in dentifrice is presented in Table 1. The Pi in dentifrice with 1% TMP and positive control were, respectively, 3374.34 ± 55.3 (mean±SD) and 1735.11 µg P/g.

Table 2 shows the mean of (%SH) after each treatment. The dentifrice supplemented with F and TMP 1% showed the lowest %SH ($p < 0.05$). The order of effect in reducing %SH was dentifrice with 500 µg F/g TMP 1% > positive control > 500 µg F/g > placebo. The same results were observed for ΔKHN, however, the order of effect in reducing was 500 µg F/g TMP 1% ~ positive control > 500 µg F/g > placebo.

Regarding F and Ca in enamel after each treatment in a layer of 50 µm removed from the enamel surface, there were no differences between dentifrice with 500 µg F/g TMP 1% and positive control ($p > 0.05$), but they were different when compared to the dentifrice with 500 µg F/g and placebo ($p < 0.05$).

The analysis of dental biofilm composition, presented in Table 3, showed that 500 µg F/g TMP 1% and the positive control dentifrice presented equal F and Ca

concentrations ($p>0.05$). The placebo dentifrice showed the lowest concentrations of F and Ca in the biofilm ($p<0.05$) and the dentifrice with 500 μg F/g differed from the others ($p<0.05$). The Pi concentration was similar in all groups, either in biofilm or enamel.

Similar results of EPS in dental biofilm were observed between 500 μg F/g TMP 1% and the positive control (Table 3, $p>0.05$). This EPS formation was lower when compared to other dentifrices ($p<0.05$).

4.5 DISCUSSION

The present study evaluated the possibility of reducing F concentration in a dentifrice in order to make it less toxic (dental fluorosis), while at the same time, maintaining a similar efficacy to a standard dentifrice (1,100 μg F/g) using an *in situ* model.

The overall data (ΔKHN , Ca and F) showed that the positive control and the 500 μg F/g TMP 1% dentifrice demonstrated similar effects on enamel demineralization and biofilm composition. Only the %SH data showed the lowest mineral loss with the 500 μg F/g TMP 1% dentifrice. The findings of the present study revealed how TMP promotes an additional effect on F action when 500 μg F/g and 500 μg F/g TMP 1% groups are compared. F and Ca content in enamel in 500 μg F/g TMP 1% were ~33% and ~24% (respectively) higher than with the 500 μg F/g dentifrice. This suggests that calcium fluoride deposition might be enhanced by the presence of TMP and during the cariogenic challenge more F and Ca were released to biofilm. Moreover, TMP causes retention of the surface zone, resulting in a more pronounced surface layer that is further enhanced by the presence of fluoride.^{16,29} Although these results do not show a TMP influence on F and/or Ca mobility into enamel, based on biochemical analysis performed in the present study; it can be suggested that TMP adsorbed on enamel alters the selective permeability and ion diffusion into the lesion.^{30,31,32} These effects could contribute to a lower mineral loss in enamel treated with TMP.

The biofilm formation on the enamel surface did not impair the effect of dentifrice treatment on enamel. However, it should be considered that treatment with dentifrice started in the first day of the experiment, when biofilm was not formed. It is assumed that dentifrice treatment was performed directly on enamel during the initial

days of each experimental phase. For this reason, this *in situ* study demonstrated the overall results considering all steps during a cariogenic challenge – starting with sound enamel until lesion and biofilm formation. F and Ca concentrations in biofilm showed that TMP increased the amount of these ions and decreased the amount of EPS, which was similar to the positive control. The highest calcium values in 500 µg F/g TMP 1% group and positive control can also be related to the lowest amount of EPS in biofilm. Ca concentration varying between 1×10^{-3} and 1×10^{-4} mol.L⁻¹ (0.04 and 0.004 µg/mg) reduces EPS concentration.³³ However, even EPS is related to bacterial adhesion and biofilm virulence.³⁴ In a microbiological study (data not published), TMP did not interfere on bacterial growth and lactic acid production on microcosm biofilm formed *in vitro*. Thus, the TMP action on biofilm could be related only to biochemical changes, with these ions interfering on biofilm, since the highest F and Ca concentrations in biofilm alter the bacterial metabolism and act in the bacterial biological activity, i.e., EPS formation.^{35,36}

Phosphorus content in biofilm seems to be not affected by sucrose frequency.^{37,38} Even though the biofilm was treated with a phosphate salt, the concentration of Pi in enamel and biofilm did not increase. Although TMP is soluble in water; it is a cyclic phosphate and seems to not be hydrolyzed in saliva or spontaneously. The amount of Pi theoretically expected in dentifrices was detected only after acid hydrolysis and it was not observed in enamel and biofilm treated with TMP. Consequently, TMP does not increase the phosphate ions availability in the oral environment. These results are similar to those demonstrated by Takeshita et al.,¹⁶ who found that a range of concentrations for TMP from 1% to 3% did not change the Pi content in enamel.

The *in situ* model used in the present study allowed evaluation of the interaction between biofilm and enamel. Even the volunteers were selected based on their enamel demineralization and biofilm formation capacity, the variables of the present study demonstrated large variation. Unlike clinical studies that require a large sample, one of the biggest advantages of *in situ* models is the use of small numbers of volunteers, 10-20, able to provide answers to questions about the caries preventive agents.³⁹ Therefore, using this *in situ* model, it can be assumed that the action of TMP can be similar between biofilm and enamel mineral changes. Therefore, the results obtained in this *in situ* study suggest that it is possible to obtain

a greater reduction in mineral loss through the supplementation of 1% TMP in a 500 µg F/ g dentifrice, maintaining a similar effect of a standard dentifrice (1100 µg F/g).

4.6 REFERENCES

1. Mascarenhas AK. Risk factors for dental fluorosis: a review of the recent literature. *Pediatr Dent* 2000; 22:269–277.
2. Browne D, Whelton H, O'Mullane D. Fluoride metabolism and fluorosis. *J Dent*. 2005; 33:177-86.
3. Horowitz HS. Commentary on and recommendations for the proper uses of fluoride. *J Public Health Dent* 1995; 55:57-62.
4. Ammari AB, Bloch-Zupan A, Ashley PF. Systematic review of studies comparing the anti-caries efficacy of children's toothpaste containing 600 ppm of fluoride or less with high fluoride toothpastes of 1,000 ppm or above. *Caries Res* 2003; 37:85-92.
5. Lima TJ, Ribeiro CCC, Tenuta LMA, Cury JA. Low-Fluoride Dentifrice and Caries Lesion Control in Children with Different Caries Experience: A Randomized Clinical Trial. *Caries Res* 2008;42:46–50
6. Harris RS, Nizel AE, Walsh BN. The effect of phosphate structure on dental caries development in rats. *J Dent Res* 1967; 46:290-294.
7. Henry CA, Navia JM. Sodium trimetaphosphate influence on the early development of rat caries and concurrent microbial changes. *Caries Res* 1969; 3:326-338.
8. Roberts AJ. Role of models in assessing new agents for caries prevention – non-fluoride systems. *Adv Dent Res* 1995, 9:304-311.
9. Gonzalez M. Effect of trimetaphosphate ions on the process of mineralization. *J Dent Res* 1971; 50:1056-1064.
10. Gonzalez M, Jeansonne BG, Feagin FF. Trimetaphosphate and fluoride actions on mineralization at the enamel-solution interface. *J Dent Res* 1973; 52:261-266.
11. McGaughey C, Stowell EC. Effects of polyphosphates on the solubility and mineralization of HA: relevance to a rationale for anticaries activity. *J Dent Res* 1977; 56:579-87.
12. Pruitt KM, Jamieson AD, Caldwell RC. Possible basis for cariostatic effect or inorganic phosphates. *Nature* 1970; 225:1249.

13. Finn SB, Frew RA, Leibowitz R, Morse W, Manson-Hing L, Brunelle J. The effect of sodium trimetaphosphate (TMP) as a chewing gum additive on caries increments in children *J Am Dent Assoc* 1978; 96: 651–655.
14. Ständtler P, Müller-Bruckschwaiger K, Schäfer F, Huntington E. The effect of sodium trimetaphosphate on caries: a 3-year clinical toothpaste trial. *Caries Res* 1996; 30:418-422.
15. O’Mullane DM, Kavanagh D, Ellwood RP, Chesters RK, Schafer F, Huntington E, Jones PR. A Three-year clinical trial of a combination of trimetaphosphate and sodium fluoride in silica toothpaste. *J Dent Res* 1997; 76:1776-1781.
16. Takeshita EM, Castro LP, Sasaki KT, Delbem, ACB. In vitro evaluation of dentifrice with low fluoride content supplemented with trimetaphosphate. *Caries Res* 2009; 43:50-56.
17. ten Cate JM. In situ models, physico-chemical aspects. *Adv Dent Res*. 1994; 8:125-33.
18. Manning RH, Edgar WM. Intra-oral models for studying de- and demineralization in man: methodology and measurement. *J Dent Res* 1992; 71 Spec No:895-900.
19. Zero DT. In situ caries models. *Adv Dent Res* 1995; 9:214-30.
20. White DJ, Featherstone JD. A longitudinal microhardness analysis of fluoride dentifrice effects on lesion progression in vitro. *Caries Res* 1987; 21:502-512.
21. Fiske CH, Subbarow Y. The colorimetric determination of phosphorus. *J Biol Chem* 1925; 66:375-400.
22. Hara AT, Queiroz CS, Paes Leme AF, Serra MC, Cury JA. Caries progression and inhibition in human and bovine root dentine in situ. *Caries Res* 2003; 37:339–344.
23. Cury JA, Rebelo MA, Del Bel Cury AA, Derbyshire MTVC, Tabchoury CP. Biochemical composition and cariogenicity of dental plaque formed in the presence of sucrose or glucose and fructose. *Caries Res* 2000; 34:491–497.
24. Weatherell JA, Robinson C, Strong M, Nakagaki H Micro-sampling by abrasion. *Caries Res* 1985; 19:97-102.
25. Nobre dos Santos M, Melo dos Santos L, Francisco SB, Cury JA. Relationship among dental plaque composition, daily sugar exposure and caries in the primary dentition. *Caries Res* 2002; 36:347-352.
26. Ccahuana-Vásquez RA, Tabchoury CPM, Tenuta LMA, Del Bel Cury AA, Vale GC, Cury JA. Effect of frequency of sucrose exposure on dental biofilm

- composition and enamel demineralization in the presence of fluoride. *Caries Res* 2007; 41:9-15.
27. Dubois M, Grilles KA, Hamilton JK, Rebers PA, Smith F. Colorimetric method for determination of sugars and related substances. *Anal Chem* 1956; 28:350-356.
 28. Campos GM. GMC 2002. Ribeirão Preto: School of Dentistry, n.d. Available at: <http://www.forp.usp.br/restauradora/gmc/gmc.htm#gmc>. Accessed on feb 21, 2002.
 29. Ingram GS, Edgar WM. Interactions of fluoride and non-fluoride agents with the caries process. *Adv Dent Res* 1994; 8:158-165.
 30. van Dijk JW, Borggreven JM, Driessens FC. The effect of some phosphates and a phosphonate on the electrochemical properties of bovine enamel. *Arch Oral Biol* 1980; 25:591-595.
 31. Tung MS, Brown WE. Characterization and modification of electrochemical properties of teeth. *J Dent Res* 1983; 62:60-64.
 32. Brown WE, Chow LC. Effects of neutral salts in a bench-scale caries model. *J Dent Res* 1986; 65:1115-1120.
 33. Boyd RF. The effect of some divalent cations on extracellular polysaccharide synthesis in *Streptococcus salivarius*. *J Dent Res* 1978; 57:380-383.
 34. Paes Leme AF, Koo H, Bellato CM, Bedi G, Cury JA. The Role of Sucrose in Cariogenic Dental Biofilm Formation—New Insight. *J Dent Res* 2006; 85:878-887.
 35. van Loveren C. Antimicrobial activity of fluoride and its in vivo importance: identification of research questions. *Caries Res* 2001; 35 (Suppl 1):65-70.
 36. Marquis RE, Clock SA, Mota-Meira M. Fluoride and organic weak acids as modulators of microbial physiology. *FEMS Microbiol Rev* 2003; 26:493-510.
 37. Pearce EI, Sissons CH, Coleman M, Wang X, Anderson SA, Wong L. The effect of sucrose application frequency and basal nutrient conditions on the calcium and phosphate content of experimental dental plaque. *Caries Res* 2002; 36:87–92.
 38. Paes-Leme AF, Dalcico R, Tabchoury CPM, Del Bel Cury AA, Rosalen PL, Cury JA. In situ Effect of Frequent Sucrose Exposure on Enamel Demineralization and on Plaque Composition after APF Application and F Dentifrice Use. *J Dent Res* 2004; 83:71-75.
 39. Featherstone JD, Zero DT. An in situ model for simultaneous assessment of inhibition of demineralization and enhancement of remineralization. *J Dent Res*. 1992; 71 Spec No:804-10.

Figure

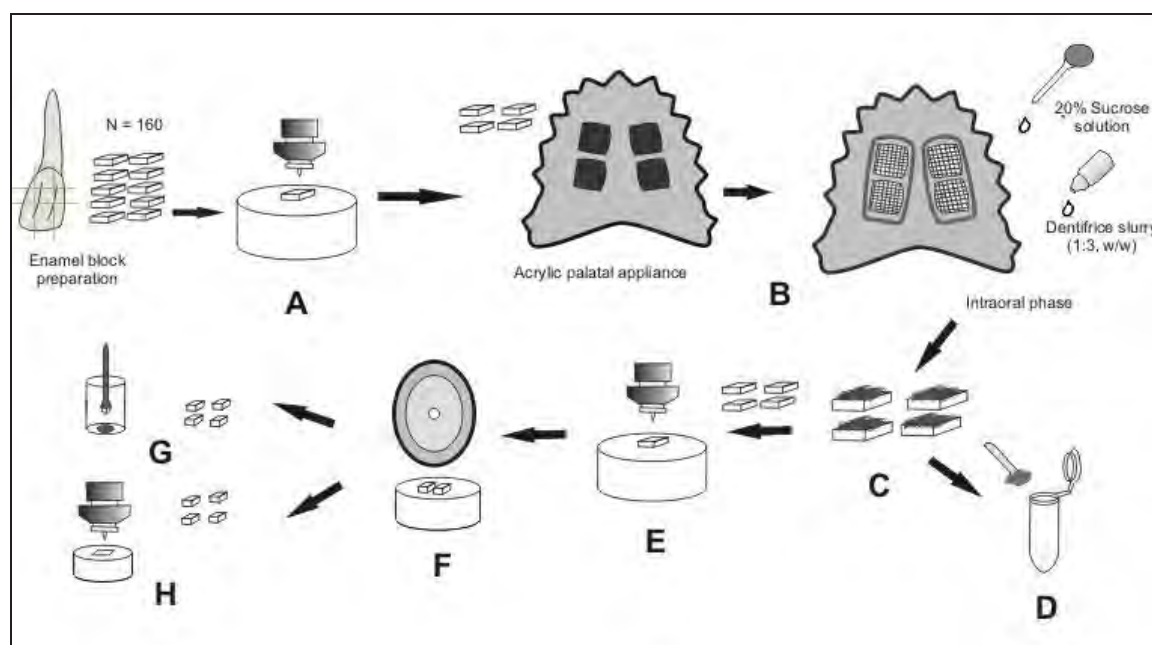


Figure 1 – **A** Enamel blocks selection through surface hardness test. **B** Acrylic palatal appliance preparation and intraoral phase. **C** After 14 days, enamel blocks and biofilm were collected from each slot of palatal appliance. **D** F, Ca, P and EPS content in biofilm analysis. **E** Surface hardness test after each phase. **F** Enamel blocks were sectioned longitudinally. **G** F, Ca and P content in enamel analysis in one of the halves of enamel block. **H** Cross-sectional hardness test in the other half of enamel block.

Tables

Table 1 - Total fluoride (FT) and ionic fluoride (FI) concentrations (mean $\pm$ SD, n=3) in dentifrices.

Groups	FT, $\mu\text{g/g}$	FI, $\mu\text{g/g}$
Placebo	12.2 $\pm$ 1.1	12.3 $\pm$ 1.7
500 μg F/g	556.7 $\pm$ 7.5	526.0 $\pm$ 19.6
500 μg F/g TMP 1%	555.4 $\pm$ 4.9	552.1 $\pm$ 3.8
Positive control	1086.2 $\pm$ 34.2	1106.3 $\pm$ 49.3

Table 2 - Fluoride (F), calcium (Ca) and phosphorus (P) concentration in enamel and percentage of change in surface hardness (%SH) and integrated loss of subsurface hardness (ΔKHN) (mean $\pm$ SD) of the enamel blocks according to the treatments.

Variable	Treatments (Dentifrices)			
	Placebo	500 μg F/g	500 μg F/g TMP 1%	Positive control
F, $\mu\text{g}/\text{mm}^3$	0.58 $\pm$ 0.15 ^a n=8	0.84 $\pm$ 0.30 ^b n=8	1.26 $\pm$ 0.47 ^c n=8	1.31 $\pm$ 0.63 ^c n=8
Ca, $\mu\text{g}/\text{mm}^3$	787.2 $\pm$ 118.8 ^a n=8	793.6 $\pm$ 272.0 ^a n=8	1,038.9 $\pm$ 96.2 ^b n=8	1,160.2 $\pm$ 164.8 ^b n=8
P, $\mu\text{g}/\text{mm}^3$	250.2 $\pm$ 117.0 ^a n=8	251.7 $\pm$ 87.6 ^a n=8	322.4 $\pm$ 51.0 ^a n=8	344.9 $\pm$ 61.9 ^a n=8
%SH	-67.1 $\pm$ 6.1 ^a n=10	-30.8 $\pm$ 13.8 ^b n=10	-9.9 $\pm$ 5.9 ^c n=18	-18.0 $\pm$ 7.6 ^d n=18
ΔKHN	7,451.3 $\pm$ 1685.3 ^a n=10	4,717.8 $\pm$ 596.5 ^b n=10	3,027.0 $\pm$ 790.7 ^c n=10	3,207.2 $\pm$ 720.8 ^c n=10

Within rows, distinct superscript letters indicate statistical significance (Kruskal-Wallis, $p < 0.05$).

Table 3 - Fluoride (F), calcium (Ca), phosphorus (P) and extracellular polysaccharides (EPS) concentration (means $\pm$ SD) in dental biofilm according to the treatments.

Variable	Treatments (Dentifrices)			
	Placebo	500 μ g F/g	500 μ g F/g TMP 1%	Positive control
F, μ g/mg	19.7 $\pm$ 5.0 ^a n=10	82.0 $\pm$ 70.2 ^b n=10	117.8 $\pm$ 79.7 ^c n=10	151.2 $\pm$ 91.0 ^c n=10
Ca, μ g/mg	2.2 $\pm$ 0.5 ^a n=10	5.1 $\pm$ 1.6 ^b n=10	7.3 $\pm$ 2.2 ^c n=10	9.4 $\pm$ 4.2 ^c n=10
P, μ g/mg	5.2 $\pm$ 1.9 ^a n=10	5.8 $\pm$ 2.1 ^a n=10	6.8 $\pm$ 3.4 ^a n=10	8.5 $\pm$ 4.1 ^a n=10
EPS, μ g/mg	298.2 $\pm$ 102.6 ^a n=10	231.1 $\pm$ 77.2 ^b n=10	134.7 $\pm$ 39.7 ^c n=10	170.8 $\pm$ 52.4 ^c n=10

Within rows, distinct superscript letters indicate statistical significance (ANOVA, Bonferroni, $p < 0.001$).

Capítulo 4



5 Remineralizing potential of a dentifrice with low fluoride content supplemented with non-fluoride alternative agent - *in situ* study.*

5.1 ABSTRACT

Objective: The use of dentifrices with low fluoride (F) content has been a way to reduce F ingestion as well as dental fluorosis. The aim of this *in situ* study was to evaluate whether a dentifrice with low F content supplemented with sodium trimetaphosphate would provide a similar remineralization potential as a standard dentifrice (1100µgF/g).

Methods: In this crossover double-blind study, eleven volunteers were selected and wore palatal appliance containing four bovine enamel blocks with artificial caries lesion. This study was performed in 4 phases during 3 days each. The treatment was carried out, *in vivo*, 3x/day during 1 min with dentifrices: placebo (negative control), 500 µgF/g, 500 µgF/g and TMP 1%, and 1100 µgF/g (positive control). After each phase, the percentage of surface hardness recovery (%SH_R) and the integrated loss of subsurface area (ΔKHN) were calculated. F, calcium (Ca) and phosphorus (P) content in enamel was determined.

Results: The results showed that the positive control and dentifrice with 500 µgF/g and TMP 1% showed similar %SH_R (ANOVA; $p>0.05$), but they were different when compared to placebo and dentifrice with low F ($p<0.05$). Regarding F and P in enamel there were no differences between dentifrice with 500 µgF/g and TMP 1% and positive control ($p>0.05$). Ca content in enamel was higher in positive control ($p<0.05$), followed by dentifrice 500 µgF/g and TMP 1%.

Conclusion: It is concluded that the dentifrice with low F supplemented with TMP 1% had similar effect as compared with a standard dentifrice in an *in situ* model.

Key-words: dentifrice, fluoride, trimetaphosphate, dental enamel, *in situ*, remineralization

*Capítulo escrito de acordo com as instruções do periódico Archives of Oral Biology (ANEXO B)

5.2 INTRODUCTION

Mineral ions in oral environment play an important role to promote enamel remineralization. They enter the oral cavity with duct saliva, foodstuffs, and crevicular fluid.¹ However, the concentration of these ions in saliva is limited and depends on individual human physiological characteristics and health conditions. Fluoride (F), calcium (Ca) and phosphate are the main minerals related to remineralization process.

Supplementation of manufactured products such as dentifrices, mouth rinses, infant formula and diet came out as a way to increase the bioavailability of these ions in oral environment. Phosphorus containing agents represent the greatest number of potential non-fluoride anticaries agents and the majority of them are phosphates.² Studies in 60's decades have shown the efficacy of phosphate salts against dental caries.^{3,4} Sodium trimetaphosphate (TMP) came out as the greatest cariostatic effect among all the phosphates tested. The order of effectiveness was: trimetaphosphate > hexametaphosphate > tripolyphosphate ~ pyrophosphate ~ orthophosphate.³

However, the mode of action of TMP on enamel remineralization remains unclear.⁵ Studies suggested that this salt is adsorbed to enamel surface reducing enamel demineralization,^{4,6,7} reducing hydroxyapatite solubility⁸ and mineral exchange,^{6,7} and changing the affinity between enamel surface and salivary proteins.⁹

Since the enhanced efficacy of F dentifrice is related to dental caries reduction as well as dental fluorosis in some countries¹⁰ the combination of low F content in dentifrice with alternative agents (i.e. phosphates salts) could be a way to maintain dentifrice efficacy similar to that of high F content (1100 µg F/g) and reduce the risk of dental fuorosis. Takeshita et al.¹¹ showed positive results testing this combination in an *in vitro* study.

Once a new formulation dentifrice has been developed, the dentifrice needs to be evaluated to ensure that the components remain active.¹² *In situ* models have been developed to test caries-preventive agents and try to replace clinical trials.¹ Since it does not have in literature *in situ* studies evaluating the effect of dentifrices with low fluoride concentration supplemented with TMP, the present study evaluated if the remineralization potential of this dentifrice would be similar to a standard dentifrice using an *in situ* model.

5.3 MATERIAL AND METHODS

Experimental Design

This crossover double blind study was previously approved by the Human Ethical Committee (protocol#2009/0807). The experimental design is displayed in figure 1. Eleven volunteers wearing acrylic palatal appliance with four enamel bovine blocks were subjected to four phases of 3 days each with 7 days washout period between each phase. Enamel blocks (4x4 mm, n=176) of bovine incisive teeth were stored in 2% formaldehyde solution (pH 7) for 30 days at room temperature.¹³ They were sequentially polished and selected through surface hardness test (330.0 up to 370.0 KHN). The blocks were demineralized and submitted to post demineralization surface hardness (SH₁). Based on the percentage of surface hardness loss the enamel blocks were allocated to four treatments: placebo (negative control), dentifrice with 500 µg F/g, dentifrice with 500 µg F/g and TMP 1% and a dentifrice with 1100 µg F/g (positive control). After each experimental period, the surface hardness (SH₂) was again assessed to calculate the percentage of surface hardness recovery (%SH_R). The blocks were sectioned to perform cross-sectional hardness test to calculate the integrated loss of subsurface area (ΔKHN). Fluoride, calcium (Ca) and phosphorus (Pi) content in enamel were also determined.

Dentifrice formulation and Fluoride and Phosphorus Assessment

The experimental dentifrices were prepared in a laboratory and had the following ingredients: carboxymethylcellulose, sodium methyl-p-hydroxybenzoate, sodium saccharin, peppermint oil, glycerol, hydrated silica, sodium lauryl sulfate and water. Fluoride (NaF, Merck, Germany) concentration in experimental dentifrice was 500 µg F/g and it was added 1% of sodium trimetaphosphate (TMP, Sigma-Aldrich Co., USA). Dentifrice without F and P (placebo, negative control) and one with 500 µg F/g and other with 1100 µg F/g (Crest™, Procter & Gamble, USA, positive control) were also used. Fluoride in dentifrices was determined using a specific electrode for F ion (9609 BN – Orion Research Inc, Beverly, MA, USA) attached to an ion analyzer (Orion 720 A+- Orion Research Inc) and calibrated with standards containing 0.125 to 2.000 µg F/g. Pi in dentifrices was measured according to the colorimetric determination as described by Fiske and Subbarow¹⁴, submitted to a previous acid hydrolysis.¹¹

Subsurface enamel demineralization

The cut surface of each enamel block was covered with a protective coating (nail varnish), except enamel. The subsurface enamel demineralization¹⁵ was produced by immersing each enamel block in 32 ml of a solution with 1.3 mmol/L Ca, 0.78 mmol/L P in 0.05 mol/L acetate buffer, pH 5.0; 0.03 ppm F; for 16h at 37°C.¹⁶

Palatal appliance preparation and treatments

The oral appliance was prepared in acrylic resin (Jet - Articles Classic Odontológico, São Paulo). Four enamel blocks with artificial caries lesion were fixed in the intraoral device in each phase. The treatments with the dentifrices were performed 3x/day, during the volunteers' habitual oral hygiene routine. The volunteers were instructed to wear their appliances 24 hours a day during each treatment period and brush their teeth with the appliance in place, using the toothbrush provided to them. Volunteers brushed for one minute during each brush and actively “swished” the dentifrice slurry around their entire mouth before expectorated. During 7-day pre-experimental period and washout periods, the volunteers brushed their teeth with nonfluoridated dentifrices. The volunteers received all the instructions previously.

Hardness Analysis

The enamel surface hardness was determined before (SH), post subsurface enamel demineralization (SH₁) and after each experimental phase (SH₂) using a Shimadzu HMV-2000 microhardness tester (Shimadzu Corp., Kyoto, Japan) under a 25g load for 10s. Five indentations spaced 100 µm from each other were made at the center of the enamel surface (SH). Indentations for post demineralization surface hardness (SH₁) and for post experiment surface hardness (SH₂) spaced 100 µm from each other and from the baseline. The percentage of surface hardness recovery (%SH_R = ((SH₂ – SH₁) / (SH – SH₁)) x 100) was calculated.

For the cross-sectional hardness measurements, the enamel blocks were longitudinally sectioned through their center and embedded in acrylic resin with the cut face exposed and gradually polished. Three sequences of fourteen indentations at different distances (5, 10, 15, 20, 25, 30, 40, 50, 70, 90, 110, 130, 220 and 330 µm) from the outer enamel surface using a Micromet 5114 hardness tester (Buehler, Lake Bluff, USA and Mitutoyo Corporation, Kanagawa, Japan) and the software

Buehler OmniMet (Buehler, Lake Bluff, USA) with a Knoop diamond indenter under a 5 g load for 10 s (X1000). The mean values at all three measuring points at each distance from the surface were then averaged.¹⁷

The integrated area above the curve (cross-sectional profiles of hardness into the enamel), using the hardness values (KHN), was calculated by trapezoidal rule (GraphPad Prism, version 3.02) in each depth (μm) from the lesion up to sound enamel. This value was subtracted from integrated area of sound enamel, to obtain the integrated area of the subsurface regions in enamel, which was named integrated loss of subsurface hardness (ΔKHN).¹¹

Fluoride, Calcium, and Phosphorus Content in Enamel

Enamel biopsy was performed according to the study by Weatherell et al.¹⁸ One of the halves of the longitudinally sectioned blocks was used obtaining blocks measuring 2X2mm. The blocks was fixed to a mandrel and fixed to the top of a modified microscope with a micrometer (Pantec, Sao Paulo, SP, Brazil) to measure the depth. Self-adhesive polishing discs (13 mm of diameter), 400 grit silicon carbide (Buehler, Lake Bluff, IL, USA) was fixed to the bottom of polystyrene crystal tubes (J-10, Injeplast, Sao Paulo, SP, Brazil). A layer of 50 μm deep of each enamel block was removed. The enamel powder was stored in tubes and 0.8 mL HCl 0.5 mol/L was added. The tubes were kept under agitation during 30 minutes and 0.8 mL NaOH 0.5 mol/L was then added. For F analysis, specific electrode Orion 9690 connected to an ion analyser (Orion 720⁺) and TISAB III (total ionic strength adjustment buffer) at 1:10 ratio (TISAB:sample) were used. For Ca analysis, the cresoftalein colorimetric method (Katal, Belo Horizonte, MG, Brazil) was used. The P was measured according to Fiske and Subbarow.¹⁴

Statistical analysis

The analysis was performed by GMC software²⁰, with a significance level of 5%. Experimental groups (placebo, 500 F, 500 F TMP 1%, positive control) were considering as variation factors and the variables were SH, SH₁, SH₂, %SH_R, ΔKHN , F, Ca and Pi. First, the normality and homogeneity of the samples were tested using, respectively, the Kolmogorov-Smirnov and Cochran tests. The data were homogeneous and were submitted to ANOVA, followed by Bonferroni test.

5.4 RESULTS

The analysis of F in dentifrice was in accordance to the concentration added. Total fluoride and ionic fluoride ($\mu\text{g/g}$) in placebo, 500 μg F/g, 500 μg F/g TMP 1% and positive control, were respectively, 12.2 ± 1.1 ; 556.7 ± 7.5 ; 555.4 ± 4.9 ; 1086.2 ± 34.2 (total fluoride) and 12.3 ± 1.7 , 526.0 ± 19.6 , 552.1 ± 3.8 , 1106.3 ± 49.3 (ionic fluoride). The phosphorus in dentifrice with TMP 1% and positive control are respectively, 3374.34 ± 55.3 (mean $\pm$ SD) and $1735.11 \mu\text{g}$ P/g.

Table 1 shows the baseline surface hardness (SH), post demineralization surface hardness (SH_1), *in situ* remineralization surface hardness (SH_2), percentage of surface hardness recovery ($\%\text{SH}_R$) according to experimental groups. No statistical differences were observed among the groups regarding SH and SH_1 . Table 2 shows the average of ΔKHN after each treatment and from the blocks that were only submitted to post demineralization surface hardness (artificial caries). The results showed that the positive control and dentifrice supplemented with F and TMP 1% showed similar $\%\text{SH}_R$ and ΔKHN ($p > 0.05$), but they were different when compared to placebo and 500 μg F/g group.

Figure 2 shows the profiles of hardness in the groups according to the depth. The blocks submitted only to post demineralization surface hardness (artificial caries) showed a demineralization area up to 120 μm . For the others groups the subsurface demineralization was more evident up to a depth of 50 μm . All groups showed enamel remineralization wherein 500 μg F/g TMP 1% and positive control groups showed the highest hardness values.

Regarding F and P in enamel after each treatment there were no differences between dentifrice with 500 μg F/g TMP 1% and positive control ($p > 0.05$), but they were different when compared to dentifrice 500 μg F/g and placebo ($p < 0.05$). Ca content in enamel was higher in positive control ($p < 0.05$), followed by dentifrice 500 μg F/g TMP 1% (Table 2).

5.5 DISCUSSION

The present study evaluated the remineralization potential of a dentifrice with low F content and supplemented with TMP 1% comparing it to a standard dentifrice (1100 μg F/g) using an *in situ* model. Since our previous *in vitro*¹¹ and an *in situ* (data not shown) studies demonstrated TMP effect avoiding enamel demineralization, the

evaluation of remineralization promoted by TMP simultaneously with F is interesting in view the fact that the mechanism of action is still unclear.^{5,21}

The subsurface demineralization produced in enamel blocks was standardized and based on the percentage of mineral loss the specimens were selected and allocated in each treatment group. By this way, all the groups started with the same mean of the percentage of mineral loss. The %SH_R and ΔKHN showed that dentifrice with 500 µg F/g and 1% TMP was similar to that of positive control (p>0.05). The same results were observed in F and P content in enamel. Differently, Ca content in enamel in positive control was slightly higher (only ~11%) than in 500 µg F/g TMP 1% group, but statistically significant (p<0.05). Comparing 500 µg F/g F and the respective supplemented group, TMP increased F, Ca and Pi in enamel, resulting in more remineralization (p<0.05). However, we have to consider that these data is related to mineral content in 50 µm layer removed from enamel surface. Above this depth, it can be observed a large remineralization area up to 120 µm when all groups are compared to the baseline.

In the solution used to produce enamel subsurface demineralization, low concentration of F (0.03 µg F/g) is added in order to form a thin surface layer allowing hardness analysis after demineralization as observed in depth profiles in the blocks submitted to subsurface demineralization only. TMP could be adsorbed to this layer reducing Ca diffusion inside the lesion⁶ and facilitating F and Pi deposition in enamel; this way, improving the quality of minerals formed⁶ and reducing subsurface lesions. TMP can cause retention of the surface zone resulting in a more pronounced surface layer that is further enhanced by the presence of F.^{11,21} By the addition of TMP 1% to 500F a more mineralized surface layer up to 10 µm depth was promoted, as shown in surface hardness and cross-sectional hardness analysis.

Since the *in situ* model designed in the present study was performed during 3 days and no additional cariogenic challenge was promoted, (for example, sucrose solution application), only remineralization was evaluated. Therefore, the calcium-phosphate solution (pH 5) used to promote subsurface demineralization, 3 days experiments were enough to evaluate differences among the groups. A recent study demonstrated that this *in situ* model was able to show verify dose-response relationship and suitable for testing low F concentration dentifrices.²³ However, considering the fact that TMP can cause slow mineral exchanges to the environment,

^{6,7} long period of experiments should be tested, and perhaps show different outcomes in Ca uptake.

Therefore, the use of low F dentifrices combined to alternative agents capable of enhance F action is an interesting way to reduce F exposure to 3 - 6 years old children, thereby reducing the risk of dental fluorosis. Further accurate studies should be carried out to evidence how TMP improves low F dentifrices efficacy. In the present *in situ* study we concluded that the supplementation with TMP in a low F dentifrice showed a similar efficacy to that of a standard dentifrice (1100 µg F/g).

5.6 REFERENCES

1. ten Cate J. In situ models, physic-chemical aspects. *Adv Dent Res* 1994; 8:125-133.
2. Foward GC. Non-fluoride anticaries agents. *Adv Dent Res* 1994; 8:208-214.
3. Harris RS, Nizel AE, Walsh BN. The effect of phosphate structure on dental caries development in rats. *J Dent Res* 1967; 46:290-294.
4. Henry CA, Navia JM. Sodium trimetaphosphate influence on the early development of rat caries and concurrent microbial changes. *Caries Res* 1969; 3:326-338.
5. Roberts AJ. Role of models in assessing new agents for caries prevention – non-fluoride systems. *Adv Dent Res* 1995, 9:304-311.
6. Gonzalez M. Effect of trimetaphosphate ions on the process of mineralization. *J Dent Res* 1971; 50:1056-1064.
7. Gonzalez M, Jeansonne BG, Feagin FF. Trimetaphosphate and fluoride actions on mineralization at the enamel-solution interface. *J Dent Res* 1973; 52:261-266.
8. McGaughey C, Stowell EC. Effects of polyphosphates on the solubility and mineralization of HA: relevance to a rationale for anticaries activity. *J Dent Res* 1977; 56:579-87.
9. Pruitt KM, Jamieson AD, Caldwell RC. Possible basis for cariostatic effect or inorganic phosphates. *Nature* 1970; 225:1249.
10. Mascarenhas AK. Risk factors for dental fluorosis: a review of the recent literature. *Pediatr Dent* 2000; 22:269–277.
11. Takeshita EM, Castro LP, Sassaki KT, Delbem, ACB. In vitro evaluation of dentifrice with low fluoride content supplemented with trimetaphosphate. *Caries Res* 2009; 43:50-56.

12. Proskin HM. Statistical considerations related to the use of caries model systems for the determination of clinical effectiveness of therapeutic agents. *Adv Dent Res* 1995; 9:270-8.
13. White DJ, Featherstone JD. A longitudinal microhardness analysis of fluoride dentifrice effects on lesion progression in vitro. *Caries Res* 1987; 21:502-512.
14. Fiske CH, Subbarow Y. The colorimetric determination of phosphorus. *J Biol Chem* 1925; 66:375-400.
15. Queiroz CS, Hara AT, Leme FP, Cury JA. pH-cycling models to evaluate the effect of low fluoride dentifrice on enamel de- and remineralization. *Braz Dent J* 2008; 19:21-27.
16. Argenta R.M, Tabchoury CP, Cury JA. A modified pH-cycling model to evaluate fluoride effect on enamel demineralization, *Pesqui Odontol Bras* 2003; 17:241-246.
17. Delbem ACB, Danelon M, Sassaki KT, Vieira AEM, Takeshita EM, Brighenti FL, Rodrigues E. Effect of rinsing with water immediately after neutral gel and foam fluoride topical application on enamel remineralization: an in situ study. *Arch Oral Biol*, in press, 2010.
18. Weatherell JA, Robinson C, Strong M, Nakagaki H. Micro-sampling by abrasion. *Caries Res* 1985; 19:97-102.
19. Campos GM. GMC 2002. Ribeirão Preto: School of Dentistry, n.d. Available at: <http://www.forp.usp.br/restauradora/gmc/gmc.htm#gmc>. Accessed on feb 21, 2002.
20. Ingram GS, Edgar WM. Interactions of fluoride and non-fluoride agents with the caries process. *Adv Dent Res* 1994; 8:158-165.
21. Delbem ACB, Afonso RL, Igreja BB, Cantagallo CF, Danellon M. In situ remineralization model to predict dose-response using low-fluoride dentifrices and bovine enamel. *Caries Res* 2010; 44:171-247

Figures

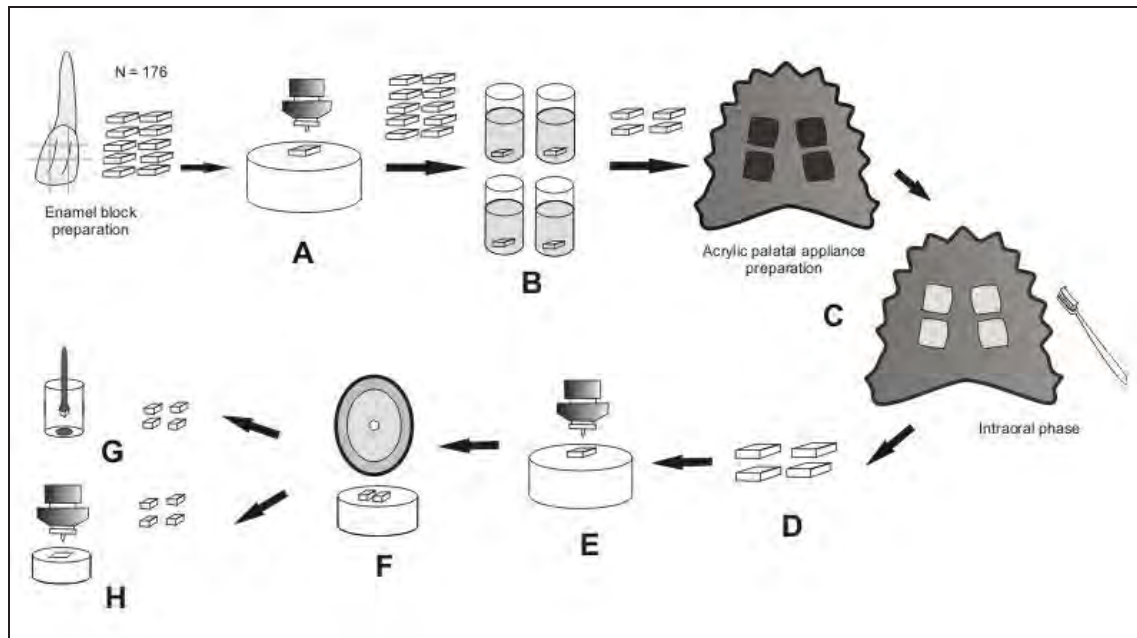


Figure 1 – **A** Enamel blocks selection through surface hardness test. **B** Subsurface enamel demineralization – Enamel block immersion in acid Ca-P solution during 16h at 37°C. **C** Acrylic palatal appliance preparation and intraoral phase – in vivo dentifrice treatment. **D** After 3-days experiment, enamel blocks are removed from palatal appliance. **E** Surface hardness test after each phase. **F** Enamel blocks were sectioned longitudinally. **G** F, Ca and P content in enamel analysis. **H** Cross-sectional hardness test.

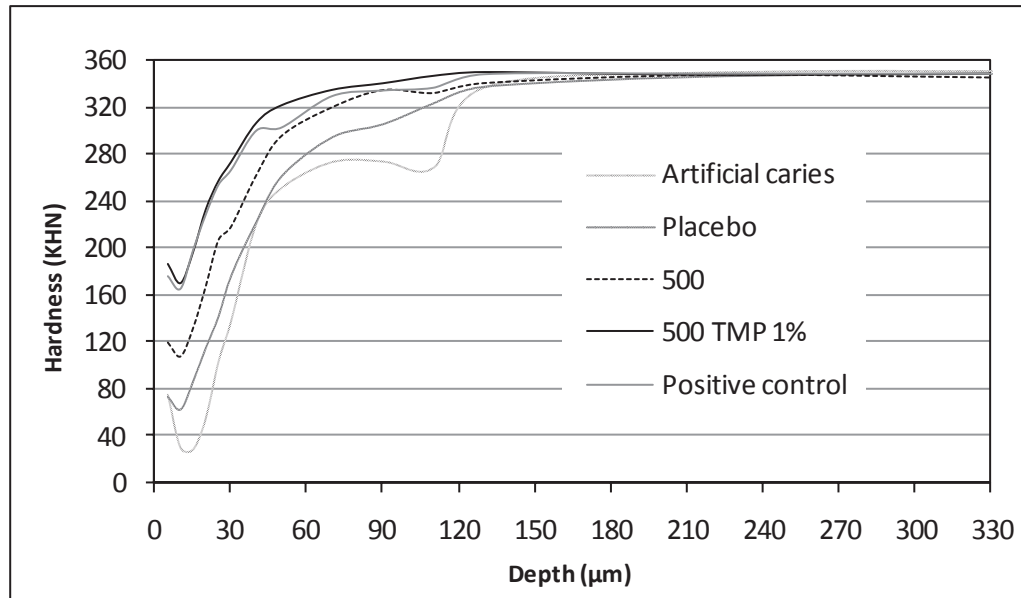


Figure 2 - Cross-sectional hardness profiles (mean KHN, n = 11) at different depths in enamel blocks according to the treatments.

Tables

Table 1 – Means ($\pm$ SD) of SH, SH₁, SH₂ and percentage of surface hardness recovery (%SH_R) and integrated loss of subsurface area (Δ KHN) in enamel blocks according to the treatments.

Variable	Treatments (Dentifrices)			
	Placebo	500 μ g F/g	500 μ g F/g TMP 1%	Positive control
SH	358.89 $\pm$ 4.44 ^a	359.8 $\pm$ 6.85 ^a	359.26 $\pm$ 5.09 ^a	360.25 $\pm$ 4.81 ^a
SH ₁	59.39 $\pm$ 2.85 ^a	66.93 $\pm$ 3.2 ^a	68.3 $\pm$ 2.72 ^a	67.5 $\pm$ 3.54 ^a
SH ₂	118.17 $\pm$ 20.14 ^a	142.93 $\pm$ 22.85 ^a	176.41 $\pm$ 23.77 ^b	175.5 $\pm$ 24.43 ^b
%SH _R	17.97 $\pm$ 6.54 ^a	25.32 $\pm$ 7.67 ^a	37.42 $\pm$ 7.41 ^b	37.39 $\pm$ 8.03 ^b

Within rows, distinct superscript letters indicate statistical significance (ANOVA, Bonferroni; SH ($p=0.937$), SH₁ ($p=0.193$), SH₂ ($p<0.05$), %SH_R ($p<0.05$)).

Table 2 – Means ($\pm$ SD) of integrated loss of subsurface area (Δ KHN) in enamel blocks according to the treatments.

Variable	Treatments (Dentifrices)				
	Artificial caries	Placebo	500 μ g F/g	500 μ g F/g TMP 1%	Positive control
Δ KHN	9647.6 $\pm$ 521.5 ^a	7828.1 $\pm$ 1032.2 ^b	5818.5 $\pm$ 1009.6 ^c	3427.6 $\pm$ 503.5 ^d	4123.6 $\pm$ 760.1 ^d

Within rows, distinct superscript letters indicate statistical significance (ANOVA, Bonferroni; $p < 0.001$).

Table 3 – Means ($\pm$ SD) of fluoride (F), calcium (Ca) and phosphorus (P) in enamel blocks according to the treatments.

Variable	Treatments (Dentifrices)			
	Placebo	500 μ g F/g	500 μ g F/g TMP 1%	Positive control
F, μ g/mm ³	0.61 $\pm$ 0.14 ^a n=11	0.95 $\pm$ 0.18 ^b n=11	1.21 $\pm$ 0.32 ^c n=11	1.44 $\pm$ 0.43 ^c n=11
Ca, μ g/mm ³	749.9 $\pm$ 92.6 ^a n=11	813.9 $\pm$ 119.2 ^a n=11	995.6 $\pm$ 132.5 ^b n=11	1126.0 $\pm$ 151.3 ^c n=11
P, μ g/mm ³	190.7 $\pm$ 16.3 ^a n=11	197.5 $\pm$ 34.6 ^a n=11	227.8 $\pm$ 23.3 ^b n=11	244.1 $\pm$ 31.3 ^b n=11

Within rows, distinct superscript letters indicate statistical significance (ANOVA, Bonferroni; $p < 0.001$).

Anexos



ANEXO A

REFERÊNCIAS BIBLIOGRÁFICAS – INTRODUÇÃO GERAL

- ADA – Council on Dental Therapeutics. Guidelines for the acceptance of fluoride-containing dentifrices. *J Am Dent Assoc* 1985; 110:45-7.
- Ammari AB, Bloch-Zupan A, Ashley PF. Systematic review of studies comparing the anti-caries efficacy of children's toothpaste containing 600 ppm of fluoride or less with high fluoride toothpastes of 1,000 ppm or above. *Caries Res* 2003; 7:85-92.
- Ashley FP. Effects of single exposure to sugar on calcium and phosphorus concentration of dental plaque. *J Dent Res* 1975; 54:1015-1018.
- Briscoe JM, Pruitt KM. Comparison of the effect of linear and cyclic phosphate on the absorption of proteins by human enamel. *J Dent Res* 1975; 54:504-507.
- Dennis DA, Gawronski TH, Cressey DE, Folke LEA. Effects of sodium trimetaphosphate supplementation of a high sucrose diet on the microbial and biochemical composition of four-day plaque and urine calcium and phosphorus levels. *J Dent Res* 1976; 55:787-196.
- Faller RN. The application of *in situ* models for evaluation of nem fluoride containing systems. *Adv Dent Res* 1995; 9:290-299.
- Featherstone JD, Zero DT. An in situ model for simultaneous assessment of inhibition of demineralization and enhancement of remineralization. *J Dent Res* 1992; 71 Spec No:804-10.
- Finn SB, Frew RA, Leibowitz R, Morse W, Manson-Hing L, Brunelle J. The effect of sodium trimetaphosphate (TMP) as a chewing gum additive on caries increments in children *J Am Dent Assoc* 1978; 96:651–655.
- Gonzalez M. Effect of trimetaphosphate ions on the process of mineralization. *J Dent Res* 1971; 50:1056-1064.
- Gonzalez M, Jeansonne BG, Feagin FF. Trimetaphosphate and fluoride actions on mineralization at the enamel-solution interface. *J Dent Res* 1973; 52:261-266.
- Harris RS, Nizel AE, Walsh BN. The effect of phosphate structure on dental caries development in rats. *J Dent Res* 1967; 46:290-294.
- Henry CA, Navia JM. Sodium trimetaphosphate influence on the early development of rat caries and concurrent microbial changes. *Caries Res* 1969; 3:326-338.
- Horowitz HS. The need for toothpastes with lower than conventional fluoride concentration for preschool-aged children. *J Public Health Dent* 1992; 52:216-221.

-
- Horowitz HS. Commentary on and recommendations for the proper uses of fluoride. *J Public Health Dent* 1995; 55:57-62.
- Ingram GS, Edgar WM. Interactions of fluoride and non-fluoride agents with the caries process. *Adv Dent Res* 1994; 8:158-165.
- Koch G, Petersson LG, Kling E, Kling L. Effect of 250 and 1000 ppm fluoridedentifrice on caries: a three-year clinical study. *Swed Dent J* 1982; 6:233-8.
- Lalumandier JA. The prevalence and risk factors of fluorosis among children in a pediatric practice in Asheville, North Carolina. *J Public Health Dent* 1992; 52:188-189.
- Larson RH, Spalter CD, Clemmer BA, Scherp HW. Continuous versus intermittent feedings of different levels of trimetaphosphate in relation to caries development in the rat. *Arch Oral Biol* 1972; 17:1537-1541.
- Mascarenhas AK. Risk factors for dental fluorosis: a review of the recent literature. *Pediatr Dent* 2000; 22:269-277.
- McGaughey C, Stowell EC. Effects of polyphosphates on the solubility and mineralization of HA: relevance to a rationale for anticaries activity. *J Dent Res* 1977; 56:579-87.
- O'Mullane DM, Kavanagh D, Ellwood RP, Chesters RK, Schafer F, Huntington E, Jones PR. A Three-year clinical trial of a combination of trimetaphosphate and sodium fluoride in silica toothpaste. *J Des Res* 1997; 76:1776-1781.
- Pendrys DG, Stamm JW. Relationship of total fluoride intake to beneficial effects and enamel fluorosis. *J Dent Res* 1990; 69:529-38.
- Pruitt KM, Jamieson AD, Caldwell RC. Possible basis for cariostatic effect of inorganic phosphates. *Nature* 1970; 225:1249.
- Roberts AJ. Role of models in assessing new agents for caries prevention – non-fluoride systems. *Adv Dent Res* 1995; 9:304-311.
- Schemehorn BR, Wood GD, Winston AE. Laboratory enamel solubility reduction and fluoride uptake from enamelon dentifrice. *J Clin Dent* 1999a; 10:9-12.
- Schemehorn BR. et al. Remineralization by fluoride enhanced with calcium and phosphate ingredients. *J Clin Dent* 1999b; 10, Spec. n.1:13-6.
- Shaw L, Murray JJ, Burchell CK, Best, J.S. Calcium and phosphorus content of plaque and saliva in relation to dental caries. *Caries Res* 1983; 17:543-548.
- Ständtler P, Müller-Bruckschwaiger K, Schäfer F, Huntington E. The effect of sodium trimetaphosphate on caries: a 3-year clinical toothpaste trial. *Caries Res* 1996; 30:418-422.
-

- Takeshita EM, Castro LP, Sasaki KT, Delbem, ACB. In vitro evaluation of dentifrice with low fluoride content supplemented with trimetaphosphate. *Caries Res* 2009; 43:50-56.
- Tanaka M, Margolis HC, Release mineral ions in dental plaque following acid production. *Arch Oral Biol* 1999; 44:253-258.
- Tanever JA, Davies RM, Ellwood RP. The prevalence and severity of fluorosis in children who received toothpaste containing either 440 or 1450 ppmF from the age of 12 months in deprived and less deprived communities. *Caries Res* 2006; 40:66-72.
- Vogel GL, Zhang Z, Carey CM, Ly A, Chow LC, Proskin HM. Composition of plaque and saliva following use of an α -tricalcium-phosphate-containing chewing gum and a subsequent challenge. *J Dent Res* 2000; 79:58-62.
- Warren JJ, Levy SM. A review of fluoride dentifrice related to dental fluorosis. *Pediatr Dent* 1999; 21:265-271.
- White DJ. The application of *in vitro* models to research on demineralization and remineralization of the teeth. *Adv Dent Res* 1995; 9:75-193.
- Zero DT. *In situ* caries models. *Adv. Dent. Res* 1995; 9:214-230.

ANEXO B

INSTRUÇÕES AOS AUTORES

Guide for Authors

A Multidisciplinary Journal of Oral & Craniofacial Sciences

Editors-in-Chief:

Dr G R Holland, Ann Arbor, MI, USA
Professor G B Proctor, London, UK

Archives of Oral Biology is an international journal which aims to publish papers of the highest scientific quality reporting new knowledge from the orofacial region including:

- developmental biology
- cell and molecular biology
- molecular genetics
- immunology
- pathogenesis
- microbiology
- biology of dental caries and periodontal disease
- forensic dentistry
- neuroscience
- comparative anatomy
- paleodontology

Archives of Oral Biology will also publish expert reviews and articles concerned with advancement in relevant methodologies. The journal will only consider clinical papers where they make a significant contribution to the understanding of a disease process.

These guidelines generally follow the Uniform Requirements for Manuscripts Submitted to Biomedical Journals

Online submission of papers

➡ <http://ees.elsevier.com/aob>

Submission and peer review of all papers is now conducted entirely online. Authors are guided stepwise through the entire process, and can follow the progress of their paper. The system creates a PDF version of the submitted manuscript for peer review, revision and proofing. All correspondence, including the editors' decision and request for revisions, is conducted by e-mail. Authors requesting further information about online submission should follow the tutorial, at

➡ <http://ees.elsevier.com/aob>

Submission of a paper implies that it has not been published previously, that it is not under consideration for publication elsewhere, and that if accepted it will not be published elsewhere in the same form, in English or in any other language, without the written consent of the publisher. Each manuscript must be accompanied by a statement signed by all authors that the manuscript in its submitted form has been read and approved by them. Authors must supply details of related papers submitted or recently published elsewhere. Submissions lacking this documentation will not be reviewed until it is supplied.

Authors are invited to suggest up to three referees they consider suitable to review their submission. The suggested reviewers should not have collaborated with the authors in the last 5 years. Full postal and email addresses should be included. The editors may or may not, at their discretion, utilize these suggestions.

Authorship

All authors should have made substantial and material contributions to the paper. These would include the individuals responsible for the conception and design of the experiments and the interpretation of data. If the work was conducted using non-institutional grant funds the Principal Investigator on the funded grant should be included in the authorship. Individuals who gave purely technical help or advise, for example, on statistical tests or provided materials such as cell lines and antibodies should be included in the Acknowledgements. 'Guest' authors are unacceptable. The Acknowledgements should also include the source of the funds used and the Principal Investigator to whom they were awarded. If the manuscript has four or more authors listed, a letter describing the contribution of each should be included. Submissions lacking this documentation will not be reviewed until they are supplied.

Conflict of interest

The potential for conflict of interest exists when an author (or the author's institution), has financial or personal relationships that may influence his or her actions. Authors are specifically asked to reflect on financial conflicts of interest (such as employment, consultancy, stock ownership, honoraria and paid expert testimony) as well as other forms of conflict of interest, including personal, academic and intellectual issues. At the end of the text, under a subheading "Conflict of interest statement" all authors must disclose any financial and personal relationships that could influence their work. Examples of potential conflicts of interest include employment, consultancies, stock ownership, honoraria, paid expert testimony, patent applications/registrations, and grants or other funding. If there are no conflicts of interest a statement confirming such should be included

Ethics

Studies on human beings.

Such studies submitted to Archives of Oral Biology should comply with the principles laid down in the Declaration of Helsinki; Recommendations guiding physicians in biomedical research involving human subjects. The declaration was adopted by the 18th World Medical Assembly, Helsinki, Finland, June 1964, amended by the 29th World Medical Assembly, Tokyo, Japan, October 1975, the 35th World Medical Assembly, Venice, Italy, October 1983, and the 41st World Medical Assembly, Hong Kong, September 1989 (→ www.wma.net/e/policy/b3.htm). The manuscript should contain a statement that the work has been approved by the appropriate ethical committees related to the institution(s) in which it was performed and that subjects gave informed consent to the work. A copy of the institutional approval should be included. Submissions lacking these documents will not be reviewed until they are supplied. Patients' and volunteers' names, initials, and hospital numbers should not be used.

Studies on animals.

The experimental procedures and care of animals should be in accordance with the European Convention for the Protection of Vertebrate Animals used for Experimental and Other Scientific Purposes (→ <http://conventions.coe.int/Treaty/en/Treaties/Html/123.htm>). The authors must state that animal care was in accordance with both these and institution guidelines. Signed documents of approval by institutional committees should be included as well as a statement from the authors that the study met the standards described in the European Convention. Submissions lacking these documents will not be reviewed until they are supplied.

Copyright

Accepted papers become the copyright of the Journal and are accepted on the understanding that they have not been published, are not being considered for publication elsewhere and are subject to editorial revision. If papers closely related to the submitted manuscript have been published or submitted for publication elsewhere, the author must state this in their cover letter. Upon acceptance of an article, authors will be asked to sign a 'Journal Publishing Agreement' (for more information on this and copyright see → <http://www.elsevier.com/authors>). Acceptance of the agreement will ensure the widest possible dissemination of information. An e-mail (or letter) will be sent to the corresponding author confirming receipt of the manuscript together with a 'Journal Publishing Agreement' form.

If excerpts from other copyrighted works are included, the author(s) must obtain written permission from the copyright owners and credit the source(s) in the article. Elsevier has preprinted forms for use by authors in these cases: please consult → <http://www.elsevier.com/permissions>

Scientific Standards

The aim of Editors and referees is to maintain a high standard of scientific communication. Normally papers are assessed by two referees selected by the Editor, and decisions regarding acceptance are based mainly upon the advice of the referees. Where appropriate, the referees' views are forwarded to the authors for their consideration. Authors may occasionally consider referees' suggestions to be ill-conceived but if their text is misunderstood by referees it is likely to be misunderstood by readers of the journal.

Types of Contribution

Original papers and review articles are welcomed. There will be no differentiation on the basis of length into full or short communications. All submissions will be refereed. Reviews may be submitted in outline prior to full submission.

Manuscript Preparation

Papers should be as concise as possible and, in view of the international character of the journal, English usages that may present difficulties to readers whose first language is not English should be avoided. The spellings used can be British or American, but must be consistent within the manuscript. Authors should express their own findings in the past tense and use the present tense where reference is made to existing knowledge, or where the author is stating what is known or concluded. Original papers should follow the pattern of: Introduction, Materials and Methods, Results or Findings, Discussion.

Authors will gain much assistance by consulting: Council of Biology Editors Style Manual Committee. Scientific Style and Format: The CBE Manual for Authors, Editors, and Publishers, 6th edition. New York: Cambridge University Press, 1994.

We suggest that authors consider using a language editing service to improve the English language usage and quality of a paper. A number of language editing companies will provide their services to our authors at competitive rates. Please follow this link for further details

→ <http://elsevier.com/wps/find/authorsview.authors/languageediting/>

The editors reserve the right to revise the wording of papers in the interest of the Journal's standards of clarity and conciseness.

General

Manuscripts must be word processed (preferably in Word format), double-spaced with wide margins and a font size of 10 or 12 points. The corresponding author should be identified (include a fax number and email address). Full postal addresses must be given for all co-authors. Please check the current style of the journal, particularly the reference style (Vancouver), and avoid excessive layout styling as most formatting codes will be removed or replaced during the processing of your article. In addition, do not use options such as automatic word breaking, justified layout, double columns or automatic paragraph numbering (especially for numbered references). The Editors reserve the right to adjust style to certain standards of uniformity. Authors should retain copies of all versions of their manuscript submitted to the journal. Authors are especially requested to be vigilant over the submission of the correct version of the manuscript at the various stages of the editorial process.

Text

Follow this order when typing manuscripts: Title, Authors, Affiliations, Abstract, Keywords, Main text (Introduction, Materials & Methods, Results, Discussion for an original paper), Acknowledgments, Appendix, References, Figure Captions and then Tables. Do not import the Figures or Tables into your text. The corresponding author should be identified with an asterisk and footnote. All other footnotes (except for table footnotes) should be identified with superscript Arabic numbers.

Title page

As titles frequently stand alone in indexes, bibliographic journals etc., and indexing of papers is, to an increasing extent, becoming computerized from key words in the titles, it is important that titles should be as concise and informative as possible. Thus the animal species to which the observations refer should always be given and it is desirable to indicate the type of method on which the observations are based, e.g. chemical, bacteriological, electron-microscopic, histochemical, etc. A "running title" of not more than 40 letters and spaces must also be supplied. A keyword index must be supplied for each paper.

Structured abstract

The paper should be prefaced by an abstract aimed at giving the entire paper in miniature. Abstracts should be no longer than 250 words and should be structured as per the guidelines published in the Journal of the American Medical Association (JAMA 1995; 273: 27-34). In brief, the abstract should be divided into the following sections: (1) Objective; (2) Design - if clinical, to include setting, selection of patients, details on the intervention, outcome measures, etc.; if laboratory research, to include details on methods; (3) Results; (4) Conclusions.

Received/accepted dates

A received date will be added to all papers when they are received by the Accepting Editor. An accepted date will also be added when the papers are received at the publishing office.

Introduction

This should be a succinct statement of the problem investigated within the context of a brief review of the relevant literature. Literature directly relevant to any inferences or argument presented in the Discussion should in general be reserved for that section. The introduction may conclude with the reason for doing the work but should not state what was done nor the findings.

Materials and Methods

Enough detail must be given here so that another worker can repeat the procedures exactly. Where the materials and methods were exactly as in a previous paper, it is not necessary to repeat all the details but sufficient information must be given for the reader to comprehend what was done without having to consult the earlier work.

Authors are requested to make plain that the conditions of animal and human experimentation are as outlined in the "Ethics" and "Studies on Animals" sections above.

Results or Findings

These should be given clearly and concisely. Care should be taken to avoid drawing inferences that belong to the Discussion. Data may be presented in various forms such as histograms or tables but, in view of pressure on space, presentation of the same data in more than one form is unacceptable.

Statistical analysis

Authors should ensure that the presentation and statistical testing of data are appropriate and should seek the advice of a statistician if necessary. A number of common errors should be avoided, e.g.: -

- Use of parametric tests when non-parametric tests are required
- Inconsistencies between summary statistics and statistical tests such as giving means and standard deviations for data which were analysed with non-parametric tests.
- Multiple comparisons undertaken with multiple t tests or non-parametric equivalents rather than with analysis of variance (ANOVA) or non-parametric equivalents.
- Post hoc tests being used following an ANOVA which has yielded a non-significant result.
- Incomplete names for tests (e.g. stating "Student's t test" without qualifying it by stating "single sample", "paired" or "independent sample")
- N values being given in a way which obscures how many independent samples there were (e.g. stating simply $n=50$ when 10 samples/measurements were obtained from each of 5 animals/human subjects).
- Stating that $P=0.000$ (a figure which is generated by some computer packages). The correct statement (in this case) is $P<0.0005$.

Discussion

This section presents the inferences drawn from the Results: these should be recapitulated only sparingly, sufficient to make the argument clear.

References

All manuscripts should use the 'Vancouver' style for references, which should be

numbered consecutively in the order in which they are first cited in the text and listed at the end of the paper.

For journal references, all authors should be included when there are six or fewer (first six followed by 'et al.' when seven or more), followed by the title of article, name of journal abbreviated according to Index Medicus, or left in full, year, volume, and first and last pages. For example:

1. N.P. Walsh, J.C. Montague, N. Callow and A.V. Rowlands, Saliva flow rate, total protein concentration and osmolality as potential markers of whole body hydration status during progressive acute dehydration in humans, *Arch Oral Biol* 49 (2) (2004), pp. 149-154.

For book references, the author(s) should be followed by the chapter title (if appropriate), editor(s) (if applicable), book title, place of publication, publisher, year and page numbers. For example:

1. A. Nanci, Ten Cate's Oral Histology: Development, Structure and Function (6th ed.), Mosby, St. Louis (2003).

Papers in the course of publication should only be entered in the references if the paper has been accepted by a journal, and then given in the standard manner in the text and list of references but with the words "In press" following the name of the journal.

Units and symbols

In general, *Archives of Oral Biology* will use the recommended SI (Système Internationale) units and symbols. The use of the litre, usually better written in full, in place of SI dm³ and ml³ in place of SI cm, will continue to be accepted. For details of the SI symbols, authors are referred to: Symbols, Signs and Abbreviations (1969) by the Royal Society of Metric and Decimal Systems in Council of Biology

Abbreviations

As *Archives of Oral Biology* is a journal with a multidisciplinary readership, abbreviations, except those universally understood such as mm, g, min. u.v., w/v and those listed below, should be avoided if possible. Examples of abbreviations which may be used without definition: ADP, AMP, ATP, DEAE-cellulose, DNA, RNA, EDTA, EMG, tris.

Other abbreviations used to improve legibility should be listed as a footnote on the title page. Chemical symbols may be used for elements, groups and simple compounds, but excessive use should be avoided. Abbreviations other than the above should not be used in titles.

Bacterial nomenclature

Organisms should be referred to by their scientific names according to the binomial system. When first mentioned the name should be spelt in full and in italics. Afterwards the genus should be abbreviated to its initial letter, e.g. '*S. aureus*' not '*Staph. aureus*'. If abbreviation is likely to cause confusion or render the intended meaning unclear, the names of microbes should be spelt in full. Only those names which were included in the Approved List of Bacterial Names, *Int J Syst Bacteriol* 1980; 30: 225-420 and those which have been validly published in the *Int J Syst Bacteriol* since 1 January 1980 have standing in nomenclature. If there is good reason to use a name that does not have standing in nomenclature, the names should be enclosed in quotation marks and an appropriate statement concerning the nomenclatural status of the name should be made in the text (for an example see *Int J Syst Bacteriol* 1980; 30: 547-556). When the genus alone is used as a noun or adjective, use lower case Roman not italic, e.g. 'organisms were staphylococci' and 'streptococcal infection'. If the genus is specifically referred to use italics e.g. 'organisms of the genus *Staphylococcus*'. For genus in plural, use lower case roman e.g. 'salmonellae'; plurals may be anglicized e.g. 'salmonellas'. For trivial names, use lower case Roman e.g. 'meningococcus'.

Numbers, measurements and statistics.

Numbers one to nine are spelled out unless they are measurements (e.g. 5 ml). Numbers greater than nine are spelled out if they begin a sentence, or when clarity requires it. Numbers above and including 10 000 have a space, not a comma. A decimal point is preceded by a number or cypher e.g. '0.5'. Decimal points in columns should be aligned vertically. Dates are usually provided in full: 14 April 1949. Measurements may be expressed in SI or non-metric units. Use 10 ml/h rather than ml.h⁻¹ or ml per h.

Drugs

These should be referred to by their approved and not proprietary names; for guidance, see the

British National Formulary. Where it is desirable to indicate a particular brand of preparation, the proprietary name and source should be given in parentheses after the proper name, e.g. testicular hyaluronidase (Testovase, Bovine Enterprises Ltd, London, UK).

Illustrations

In the initial online submission and review stage, authors are required to provide electronic versions of their illustrations. When an article has been accepted, authors must be prepared to provide all illustrations in electronic and camera-ready format, (suitable for reproduction, which may include reduction, without retouching).

The Artwork Quality Control Tool is now available to users of the online submission system. To help authors submit high-quality artwork early in the process, this tool checks the submitted artwork and other file types against the artwork requirements outlined in the Artwork Instructions to Authors on www.elsevier.com/arkworkinstructions. The Artwork Quality Control Tool automatically checks all artwork files when they are first uploaded. Each figure/file is checked only once, so further along in the process only new uploaded files will be checked.

General: Information relating to the preferred formats for artwork and illustrations may be found at www.elsevier.com/authors. Photographs, charts and diagrams are all to be referred to as "Figure(s)" and should be numbered consecutively in the order to which they are referred. They should accompany the manuscript, but should not be included within the text. All figures are to have a caption. Captions should be supplied on a separate page.

Line drawings: All lettering, graph lines and points on graphs should be sufficiently large and bold to permit reproduction when the diagram has been reduced to a size suitable for inclusion in the journal. Dye-line prints or photocopies are not suitable for reproduction. Do not use any type of shading on computer-generated illustrations.

Photographs: Original photographs must be supplied as they are to be reproduced (e.g. black and white or colour). If necessary, a scale should be marked on the photograph. Please note that photocopies of photographs are not acceptable.

Colour: Certain illustrations will be approved for publication in colour but only if, in the opinion of the Editors, the figures convey information not apparent in monochrome. Please note that figures supplied in colour will appear online in colour at no extra charge, even if the print version is monochrome.

Tables: Tables should be numbered consecutively and given a suitable caption. Begin each table on a separate page. Footnotes to tables should be typed below the table and referred to by superscript lowercase letters. No vertical rules should be used. Tables should not duplicate results presented elsewhere in the manuscript (e.g. in graphs).

Revised manuscripts Frequently authors are required to submit revised versions of manuscripts in the light of reports from expert reviewers and editorial comments. Revised manuscripts must clearly show revisions and authors must clearly indicate the positions of revisions in a covering letter that addresses the concerns of reviewers/ editors.

Proofs One set of page proofs in PDF format will be sent by e-mail to the corresponding author which they are requested to correct and return within **48 hours**. Only minor corrections are acceptable at this stage. Please use this proof only for checking the typesetting, editing, completeness and correctness of the text, tables and figures. If we do not have an e-mail address then paper proofs will be sent by post. Elsevier now sends PDF proofs that can be annotated; for this you will need to download Adobe Reader version 7 available free from <http://www.adobe.com/products/acrobat/readstep2.html> Instructions on how to annotate PDF files will accompany the proofs. The exact system requirements are given at the Adobe site: <http://www.adobe.com/products/acrobat/acrrsystemreqs.html#70win>. If you do not wish to use the PDF annotations function, you may list the corrections (including replies to the Query Form) and return to Elsevier in an e-mail. Please list your corrections quoting the line number. If, for any reason, this is not possible, then mark the corrections and any other comments (including replies to the Query Form) on a printout of your proof and return by fax, or scan the pages and e-mail, or by post.

Please use this proof only for checking the typesetting, editing, completeness and correctness of the text, tables and figures. Significant changes to the article as accepted for publication will only

be considered at this stage with permission from the Editor. We will do everything possible to get your article published quickly and accurately. Therefore, it is important to ensure that all of your corrections are sent back to us in one communication: please check carefully before replying, as inclusion of any subsequent corrections cannot be guaranteed. Proofreading is solely your responsibility. Note that Elsevier may proceed with the publication of your article if no response is received.

Offprints

The corresponding author, at no cost, will be provided with a PDF file of the article via e-mail or, alternatively, 25 free paper offprints. The PDF file is a watermarked version of the published article and includes a cover sheet with the journal cover image and a disclaimer outlining the terms and conditions of use. Additional paper offprints can be ordered by the authors. An order form with prices will be sent to the corresponding author.

Funding body agreements and policies

Elsevier has established agreements and developed policies to allow authors who publish in Elsevier journals to comply with potential manuscript archiving requirements as specified as conditions of their grant awards. To learn more about existing agreements and policies please visit

➡ <http://www.elsevier.com/fundingbodies>.

Author enquiries

For enquiries relating to the submission of articles please visit ➡ www.elsevier.com/authors. This website provides information on article submission as well as detailed artwork guidelines, copyright information, frequently asked questions and more. Further questions may be directed to the journal editorial office: *Archives of Oral Biology*, Elsevier Ltd, Bampfylde Street, Exeter, EX1 2AH, UK. Email: aob@elsevier.com

ANEXO C

COMITÊ DE ÉTICA – CAPÍTULO 1



UNIVERSIDADE ESTADUAL PAULISTA
"JÚLIO DE MESQUITA FILHO"
Campus de Araçatuba



COMITÊ DE ÉTICA EM PESQUISA – CEP-

OF. 105/2007
CEP
SFCD/bri

Araçatuba, 08 de agosto de 2007.

Referência Processo FOA 2007-01367

O Coordenador do Comitê de Ética em Pesquisa desta Unidade, tendo em vista o parecer favorável da relatora que analisou o projeto "AVALIAÇÃO "IN SITU" DA AÇÃO ANTICARIOGÊNICA DE DENTIFRÍCIOS DE BAIXA CONCENTRAÇÃO FLUORETO E SUPLEMENTADO COM FOSFATO" expede o seguinte parecer:

Aprovado:

Informamos a Vossa Senhoria que de acordo com as normas contidas na resolução CNS 215, deverá ser enviado relatórios parciais em 02/08/2008; 02/08/2009; 02/08/2010 e o relatório final em 02/08/2011.

Prof. Dr. Stefan Fiúza de Carvalho Dekon
Coordenador do CEP

Ilmo. Senhor
Dr. ALBERTO CARLOS BOTAZZO DELBEM
Araçatuba-SP-

Ciente. De acordo.
17/08/07
Dr. Alberto Carlos Botazzo Delbem

ANEXO D

COMITÊ DE ÉTICA – CAPÍTULO 2



UNIVERSIDADE ESTADUAL PAULISTA
"JÚLIO DE MESQUITA FILHO"
Campus de Araçatuba

COMITÊ DE ÉTICA EM PESQUISA – CEP

CERTIFICADO

Certificamos que o Projeto **“Avaliação in situ da ação anticariogênica de dentifrícios de baixa concentração de fluoreto e suplementados com fosfato sobre remineralização do esmalte”**, sob a responsabilidade de Alberto Carlos Botazzo Delbem está de acordo com os Princípios Éticos em Pesquisa e foi aprovado em 16/4/09, de acordo com o Processo FOA-0807/09.

Araçatuba, 24 de abril de 2009.




ALESSANDRA MARCONDES ARANEGA
Vice-Coordenadora do CEP

Faculdade de Odontologia e Curso de Medicina Veterinária - Seção Técnica Acadêmica
Rua José Bonifácio, 1193 CEP 16015-050 Araçatuba – SP
Tel (18) 3636-3225 E-mail: cep@foa.unesp.br


ANEXO E

DOSAGEM DE F NOS DENTIFRÍCIOS – CAPÍTULO 1 E 2

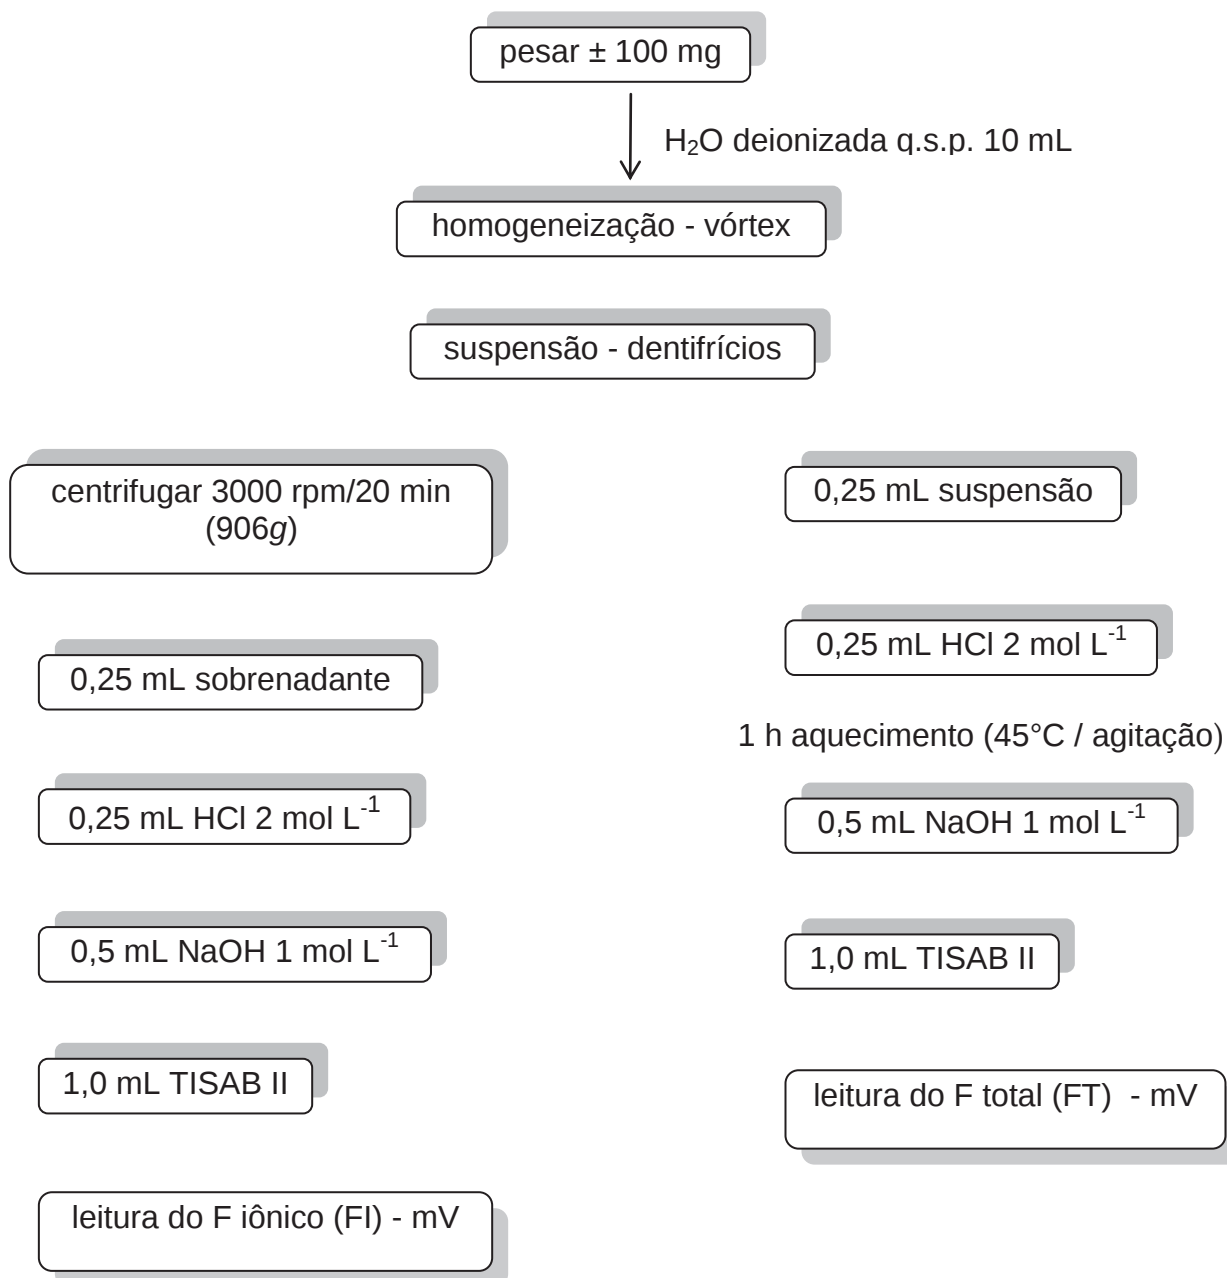

ANEXO F

DOSAGEM DE P NOS DENTIFRÍCIOS – CAPÍTULO 1 E 2

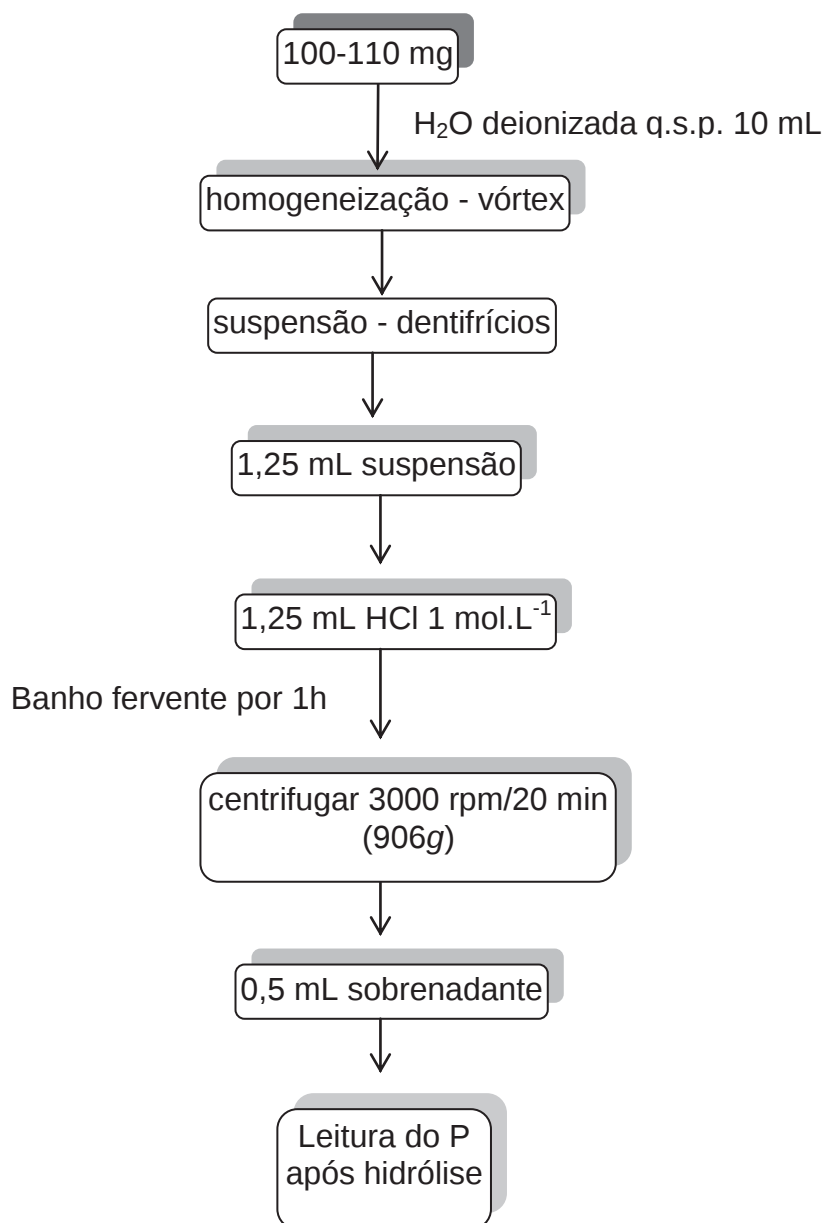


ANEXO G

DETERMINAÇÃO DE F, Ca, P e EPS NO BIOFILME – CAPÍTULO 1



1. Após 14 dias, foi realizada a coleta do biofilme formado. O biofilme de cada slots foi analisado separadamente e depois calculado a média para cada fase de cada voluntário.

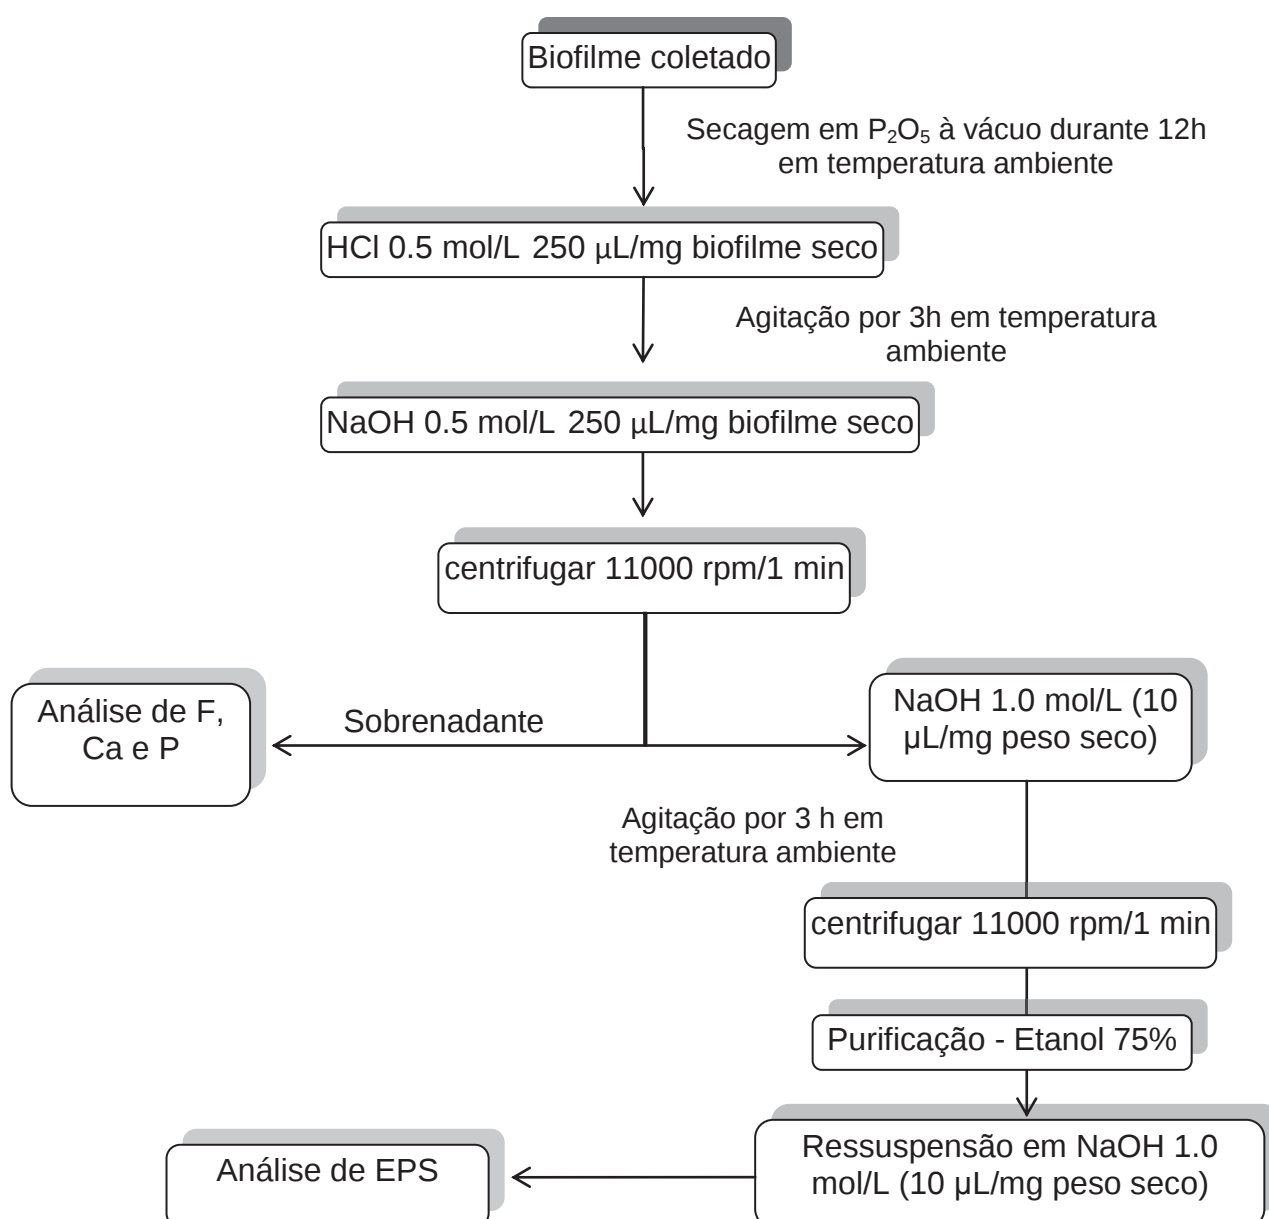


ANEXO H


PREPARO E SELEÇÃO DOS BLOCOS DE ESMALTE (4 x 4 mm)




2. Coroa do dente bovino incisivo central inferior, separada da raiz através de disco diamantado de duas faces (KG Sorensen D 91), montado em motor de bancada (Nevoni), mantido sob refrigeração (água destilada/deionizada).

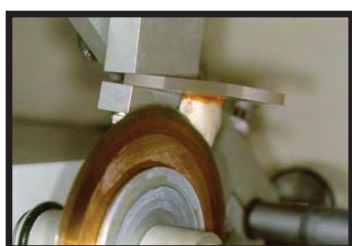


3. Secção da coroa utilizando disco diamantado (série 15 HC Diamond - n. 11-4244 Buehler) separando a superfície vestibular da lingual.

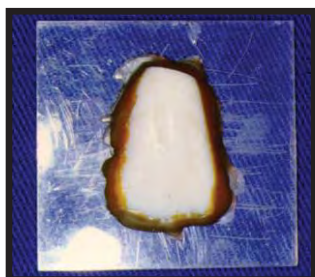

4. Face vestibular fixada na placa de acrílico.

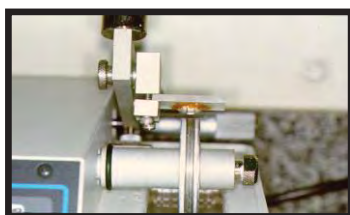



5. Secção da face vestibular no sentido longitudinal, na porção mais plana, utilizando-se 2 discos diamantados (série 15 HC Diamond –n. 11-4243 Buehler), montados em cortadeira sob refrigeração com água destilada/deionizada e separados por um disco espaçador de alumínio com 4 mm de espessura. Em seguida, foi realizado o corte no sentido transversal.

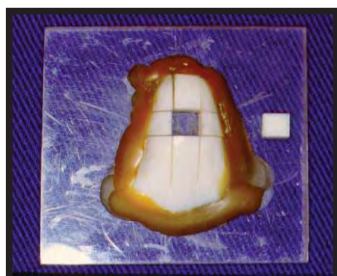

6. Fragmento vestibular do dente bovino, fixado sobre placa de resina. Ao lado, bloco de esmalte dentário.
-

ANEXO I

PREPARO E SELEÇÃO DOS BLOCOS DE ESMALTE*Planificação da dentina e polimento do esmalte*

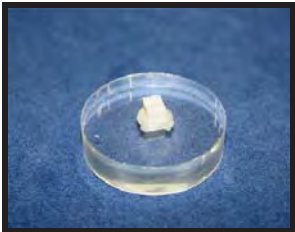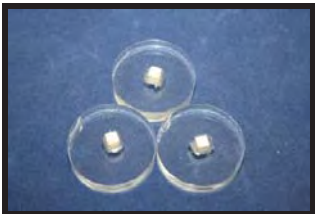	1. Bloco de esmalte fixado em disco de resina acrílica pré-fabricada (± 3 cm de diâmetro por ± 8 mm de espessura), com auxílio de cera pegajosa (Kota Ind. e Com. LTDA), com a superfície dentinária voltada para cima.
2. Ajuste da dentina para obtenção de superfícies paralelas entre esmalte e dentina, utilizando Politriz APL-4 AROTEC e lixas de granulação 320 (CARBIMET Paper Discs, 30-5108-320, BUEHLER), 2 pesos, durante 20 segundos sob baixa rotação e refrigeração.	
	3. Blocos fixados com a superfície do esmalte voltada para cima, a qual será polida.

Seqüência do polimento de esmalte:

1. Pedra-pomes, água deionizada e taça de borracha montada em contra-ângulo em baixa-rotação.
2. Na Politriz APL-4 AROTEC - lixa de granulação 600, 800 e 1200 (30 segundos – 2 pesos) e refrigeração a água. Limpeza em lavadora ultrassônica e água destilada/deionizada por 2 minutos, entre cada lixa;
3. Na Politriz APL-4 AROTEC - acabamento final com disco de papel feltro TEXMET 1000 (Buehler Polishing Cloth) (1 minuto – 2 pesos) e suspensão de diamante 1 micron base-água (Buehler);
4. Limpeza em lavadora ultrassônica utilizando solução detergente (Ultramet Sonic Cleaning Solution - Buehler) diluída 20:1 em água destilada/deionizada (2 minutos);
5. Lavagem durante 30 segundos com jato de água destilada/deionizada.

ANEXO J

ANÁLISE DE MICRODUREZA



1. Microdurômetro Shimadzu Micro Hardness Tester HMV-2.000 (Shimadzu Corporation - Kyoto-Japan), com penetrador tipo Knoop, acoplado ao Software para análise de imagem CAMS-WIN (NewAge Industries, USA).


2. Bloco de esmalte sendo submetido à leitura no microdurômetro, carga estática de 25 gramas e tempo de 10 segundos, para análise da microdureza de superfície.



3. Fotomicrografia das impressões para análise de microdureza de superfície inicial (SMH-inicial), e final (SMH-final) (Aumento: 100x).

ANEXO K

MICRODUREZA EM SEÇÃO LONGITUDINAL

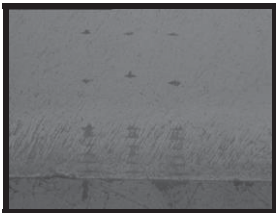	1. Embutidora metalográfica (AROTEC PRE 30S) – utilizada para inclusão dos blocos de esmalte em 5 gramas de resina acrílica (Buehler Transoptic Powder, Lake Bluff, Illinois, USA), pressão de 150 Kgf/cm², tempo de aquecimento de 7 minutos e mais 7 minutos de resfriamento. Os blocos foram fixados em posição com cola adesiva (Super Bonder – Loctite).
	2. Corpo de prova – plano longitudinal voltado para a superfície da resina acrílica.
	3. Microdurômetro Shimadzu Micro Hardness Tester HMV-2.000 (Shimadzu Corporation - Kyoto-Japan), com penetrador tipo Knoop, acoplado ao Software para análise de imagem CAMS-WIN (NewAge Industries, USA).
	4. Fotomicrografia das impressões para análise de microdureza de secção longitudinal nas diferentes distâncias. (Aumento: 100x).

Seqüência do polimento de esmalte:

1. Na Politriz APL-4 AROTEC - lixa de granulação 320 (1 minuto – 2 pesos), 600, 800 e 1200 (2 minutos – 2 pesos) e refrigeração a água. Limpeza em lavadora ultrassônica e água destilada/deionizada por 2 minutos, entre cada lixa;
2. Na Politriz APL-4 AROTEC - acabamento final com disco de papel feltro MICROCLOTH SUPREME PSA (Buehler Polishing Cloth) (2 minuto – 2 pesos) e suspensão de diamante 1/4 micron base-água (Buehler);
3. Limpeza em lavadora ultrassônica utilizando solução detergente (Ultramet Sonic Cleaning Solution - Buehler) diluída 20:1 em água destilada/deionizada (3 minutos);
4. Lavagem durante 30 segundos com jato de água destilada/deionizada.


ANEXO L

MICROABRASÃO



1. Micrômetro acoplado ao aparelho de microscópio modificado.

2. Bloco de esmalte adaptado ao mandril, sendo submetido à microabrasão, com desgaste de 50 μm , para análise da incorporação de F, Ca e P no esmalte.

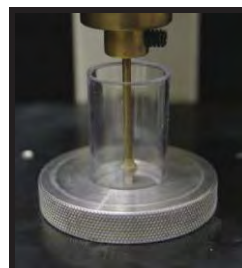

3. Após desgaste, pó de esmalte presente na lixa adaptada em frascos de poliestireno cristal (J-10, Injeplast).

ANEXO M

CICLAGEM DE pH e MICRORRADIOGRAFIA TRANSVERSAL – CAPÍTULO 3




1. Sistema robótico para ciclagem de pH.



2. Secção dos espécimes em espessura aproximada de 400µm em cortadeira - Well type 3242, Ebner, Mannheim, Germany.



3. Desgaste bilateral das secções até espessura de aproximadamente 100µm. Abrasivo - partículas de 3µm de Al₂O₃ (Logitech PM4)

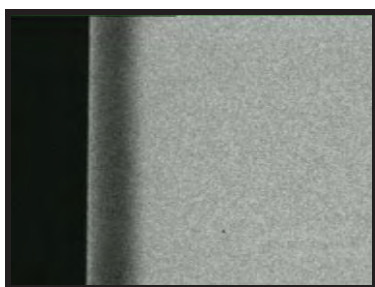

4. Análise: TMR software 1.25, Inspektor Research Systems